

SKB

TECHNICAL
REPORT

87-08

**An approach for evaluating the
general and localized corrosion
of carbon steel containers for
nuclear waste disposal**

GP March, KJ Taylor, SM Sharland, PW Tasker
Harwell Laboratory, Oxfordshire

June 1987

SVENSK KÄRNBRÄNSLEHANTERING AB
SWEDISH NUCLEAR FUEL AND WASTE MANAGEMENT CO
BOX 5864 S-102 48 STOCKHOLM
TEL 08-665 28 00 TELEX 13108-SKB

AN APPROACH FOR EVALUATING THE GENERAL AND LOCALIZED
CORROSION OF CARBON STEEL CONTAINERS FOR NUCLEAR WASTE
DISPOSAL

G P Marsh, K J Taylor, S M Sharland and P W Tasker
Harwell Laboratory, Oxfordshire

June 1987

This report concerns a study which was conducted for SKB. The conclusions and viewpoints presented in the report are those of the author(s) and do not necessarily coincide with those of the client.

Information on KBS technical reports from 1977-1978 (TR 121), 1979 (TR 79-28), 1980 (TR 80-26), 1981 (TR 81-17), 1982 (TR 82-28), 1983 (TR 83-77), 1984 (TR 85-01), 1985 (TR 85-20) and 1986 (TR 86-31) is available through SKB.

AN APPROACH FOR EVALUATING THE GENERAL AND LOCALISED CORROSION OF CARBON STEEL CONTAINERS FOR NUCLEAR WASTE DISPOSAL

G.P. MARSH*, K.J. TAYLOR*, S.M. SHARLAND# AND P.W. TASKER#

* Materials Development Division, # Theoretical Physics Division, Harwell Laboratory, Oxfordshire, OX11 0RA, U.K.

ABSTRACT

The paper considers the long term corrosion of carbon steel containers for heat generating nuclear waste in a granitic repository. Under such conditions carbon steel may exhibit general, localised or passive corrosion behaviour depending on the exact composition and redox potential of the groundwater contacting the containers; localised corrosion being of most concern because it has the fastest propagation rate. It is well established, however, that such localised corrosion is only possible when the environment is sufficiently oxidising to maintain a positive potential gradient between the cathodic surface and the corrosion sites, which requires that species with oxidising potentials greater than water need to be present. This fact provides a basis for estimating the periods during which containers may be subject to localised and subsequently to general corrosion, and hence for making an overall assessment of the metal allowance required for a specified container life. A model for the diffusion transport of oxygen has been developed, and a sensitivity analysis has shown that the period of possible localised attack is strongly dependent on the passive film leakage current, the radiation dose rate and the oxygen diffusion coefficient.

INTRODUCTION

Conceptual designs for the disposal of heat generating nuclear waste in geological formations generally include the provision of a container, which is intended to isolate the waste for the order of 500 to 1000 years. The use of carbon steel for the production of such containers has the advantage of avoiding the difficult task of demonstrating long term corrosion resistance [1]. It does, however, require knowledge of the type of corrosion which will occur, and its rate of propagation, so that an appropriate allowance can be specified. In previous publications the forms of corrosion considered possible in granitic repository environments were listed as; general corrosion, localised attack, stress corrosion cracking, hydrogen embrittlement and microbial induced corrosion [1,2]. On the basis of more recent work it has been concluded that stress corrosion cracking should be avoided by stress relieving the containers [3,4], and that hydrogen embrittlement can also be avoided providing the closure weld heat-affected-zone is softened by heat treatment [3,5]. Given this position, attention has focussed on general and localised corrosion with a combination of mathematical modelling and experimental studies aimed at evaluating the rates of these processes as a function of disposal time [6,7].

Because localised corrosion propagates more rapidly than general attack in granitic environments, it will dominate estimation of the corrosion allowance. Therefore, if the corrosion allowance is not to be over conservative, it is important to know for what fraction of the container life localised corrosion may occur. This paper describes a mechanistically based approach for making such an estimate, and a sensitivity analysis to establish which factors control the period of localised attack.

MECHANISM OF LOCALISED CORROSION

First of all it is important to make clear what is meant by localised corrosion because the corrosion literature contains many examples where this term is used to describe the points of maximum penetration on what is essentially an uneven general corrosion front. In the present instance localised corrosion refers to the isolated penetrations which may develop as pits or at crevices on otherwise passive metal surfaces.

This form of corrosion in carbon steel has been studied extensively by Pourbaix [8], who determined the chemical and electrochemical conditions associated with pitting attack using electrochemical polarisation techniques, and depicted these on potential-pH diagrams. We have made similar measurements in Na_2CO_3 - NaHCO_3 - NaCl solutions at 50°C [3,6], and the results from 0.01M CO_3^{2-} - HCO_3^- solution are superimposed on the theoretical potential-pH diagram for the $\text{Fe-H}_2\text{O}$ 0.01M CO_3^{2-} system [9] in figure 1(a). The important points to note are that pitting occurs at a potential somewhat above the passivation potential, that this potential increases with pH, and that pitting does not occur at low pH's because the steel cannot passivate.

The experimentally determined boundary between stability and general corrosion runs parallel to the theoretical equilibrium for the Fe-FeCO_3 reaction, but about 50 mV more positive. This represents a reasonably good correlation bearing in mind that the experimental results are for 50°C and the theoretical values for 25°C . Furthermore, the experimental boundary is based on the potentials of zero net current on a mixed reaction surface, which would be expected to be higher than the thermodynamic equilibrium for the anodic reaction alone because of the cathodic current component arising from water reduction. In contrast, there is no clear link between the empirical general corrosion-passivation boundary and any of the thermodynamic equilibria, although it does appear to have a similar pH relationship as the $\text{Fe-Fe}_3\text{O}_4$ and $\text{Fe}_3\text{O}_4\text{-Fe}_2\text{O}_3$ equilibria. No analyses have been performed in the present study, but the literature contains evidence that the passive film is Fe_3O_4 [10,11].

The mechanism whereby localised corrosion develops on passive surfaces of metals such as carbon steel and stainless steel has been the subject of considerable research [12]. Even so there continues to be much debate on the initiation process, although a consensus has been achieved on how the pits remain stable and propagate, the essential features of which are as follows:

- (a) At the end of the initiation stage the environment at the localised corrosion site has become sufficiently acidic to cause the metal to corrode actively. This results in the development of a potential gradient between the active sites and the remaining passive surface.
- (b) Because the passive surface is more noble than the localised active sites it supplies part of the cathodic current required to sustain dissolution in these sites. As a result anions such as OH^- , Cl^- and SO_4^{2-} migrate into the active sites.
- (c) The migration of Cl^- and SO_4^{2-} into the active sites results in the formation of FeCl_2 and FeSO_4 which hydrolyse to produce HCl and H_2SO_4 . This maintains the acidity of the sites, thus sustaining the localised corrosion process.

This mechanism has been supported by direct measurements of the pH in localised corrosion sites, which in the case of carbon steel is in the region of 3-4 [13,14,15]; in good agreement with theoretical estimates based

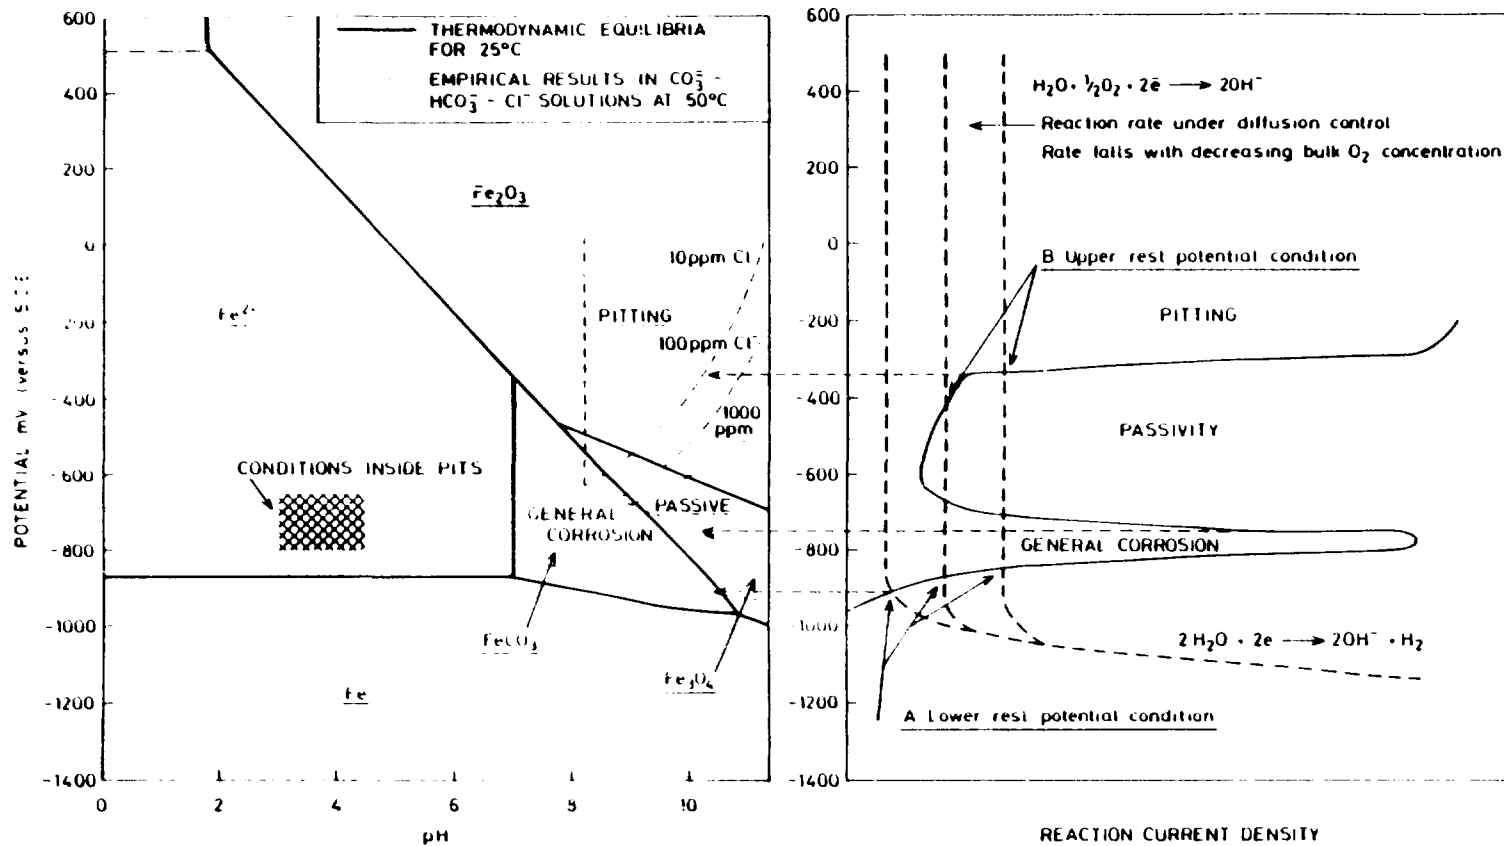


Figure 1 (a) Potential-pH diagram comparing the thermodynamic equilibria of the Fe-H₂O 0.01M²CO₃ system [i.e. for a metal ion concentration of 10⁻⁶ M litre⁻¹] with experimentally determined conditions for general corrosion, passivity and localised corrosion in 0.01M CO₃²⁻-HCO₃⁻ solutions.

(b) Schematic anodic and cathodic polarisation curves illustrating how the rest potential of carbon steel is influenced by oxygen supply in 0.01M CO₃²⁻ + 10 ppm Cl⁻ solution.

on the hydrolysis of FeCl_2 [15]. The electrode potential within localised corrosion sites has also been measured and has been shown to be more active than the surrounding passive surface [15]. Using the data from these measurements the approximate conditions within a localised corrosion site have been indicated by a cross-hatched zone in figure 1(a). This indicates the potential difference existing between the active areas and the passive surface when carbon steel is subject to localised attack.

In practice the open surface potential and pH conditions associated with localised corrosion change depending on the relative concentrations of passivating (e.g. HCO_3^- , CO_3^{2-}) and aggressive (e.g. Cl^- , SO_4^{2-}) ions. This means that the possibility of carbon steel containers being subject to localised attack can only be assessed after the repository environment has been fully characterised. However, the mechanism for the propagation of localised corrosion outlined above indicates one fundamental condition for the occurrence of such attack, which is that it will cease when the external surface is no longer cathodic (i.e. positive) to the active sites. Without a supply of cathodic current from the external surface all the cathodic reaction required to sustain dissolution will have to occur within the active site. This will result in the consumption of acidity, which will no longer be regenerated by hydrolysis, because there is no potential gradient to cause the migration of Cl^- or SO_4^{2-} ions into the active sites. This forms a basis for estimating the maximum period during which the containers may be subject to localised attack.

The factors which determine the overall potential of a carbon steel surface are illustrated by the reaction current versus potential diagrams in figure 1(b). The solid line indicates the rate of the anodic (i.e. corrosion) reaction which, with increasing potential, goes through transitions from general corrosion to passivity to localised corrosion. The broken line depicting the cathodic reaction rate is based on the assumption that the main cathodic reactants under repository conditions will be oxygen and water. The electrode potential of the metal is determined by the charge neutrality requirement that the algebraic sum of the anodic and cathodic reaction currents should be zero. Figure 1(b) shows that at low and zero oxygen levels this condition is only met at the points marked A where the metal is subject to general attack. However, when oxygen is present the rest potential may be at points A or B depending on the rate of the oxygen reduction reaction. The minimum requirement for maintaining the steel at a passive or possibly pitting potential (i.e. B) is that the oxygen reduction rate is at least equal to the rate of metal dissolution through the passive film.

Comparison of rest potentials A and B with the electrode potential in a localised corrosion sited (figure 1(a)) shows that A is more negative and B more positive. This leads to the not unreasonable conclusion that carbon steel can only be subject to localised corrosion when in the passive state. The above conclusion has been investigated experimentally by a series of tests in 0.1M NaHCO_3 + 1000 ppm Cl^- solution (pH 8.3) at 90°C using a carbon steel of composition 0.17% C, 0.75% Mn, 0.06% Si, 0.02% S and 0.002% P. Previous work [3] has shown that this environment causes pitting at 0, -200 and -400 mV (SCE), and these additional experiments were undertaken to determine the lower potential limit for pitting attack. Results for tests lasting 600h are illustrated in figure 2 which indicates a limiting potential of -600 mV, which is approximately 150 mV above the passivation potential for this solution.

It is worth mentioning one important exception to the above analysis which is the localised corrosion of boiler tube steels in highly deoxygenated water. The key difference here is that the high heat flux causes the concentration of corrosive salts in pores and fissures in the protective Fe_3O_4 layer. The heat flux from heat emitting waste containers

is much lower than for boiler tubes and therefore this mechanism should not be operative under repository conditions.

With this exception it is clear from the above that the maximum period for localised corrosion can be estimated by calculating the rate of transport of oxygen to the containers as a function of time. The minimum requirement for passivity, and hence possible localised attack, is that the oxygen reduction rate should be at least equal to the passive metal dissolution rate.

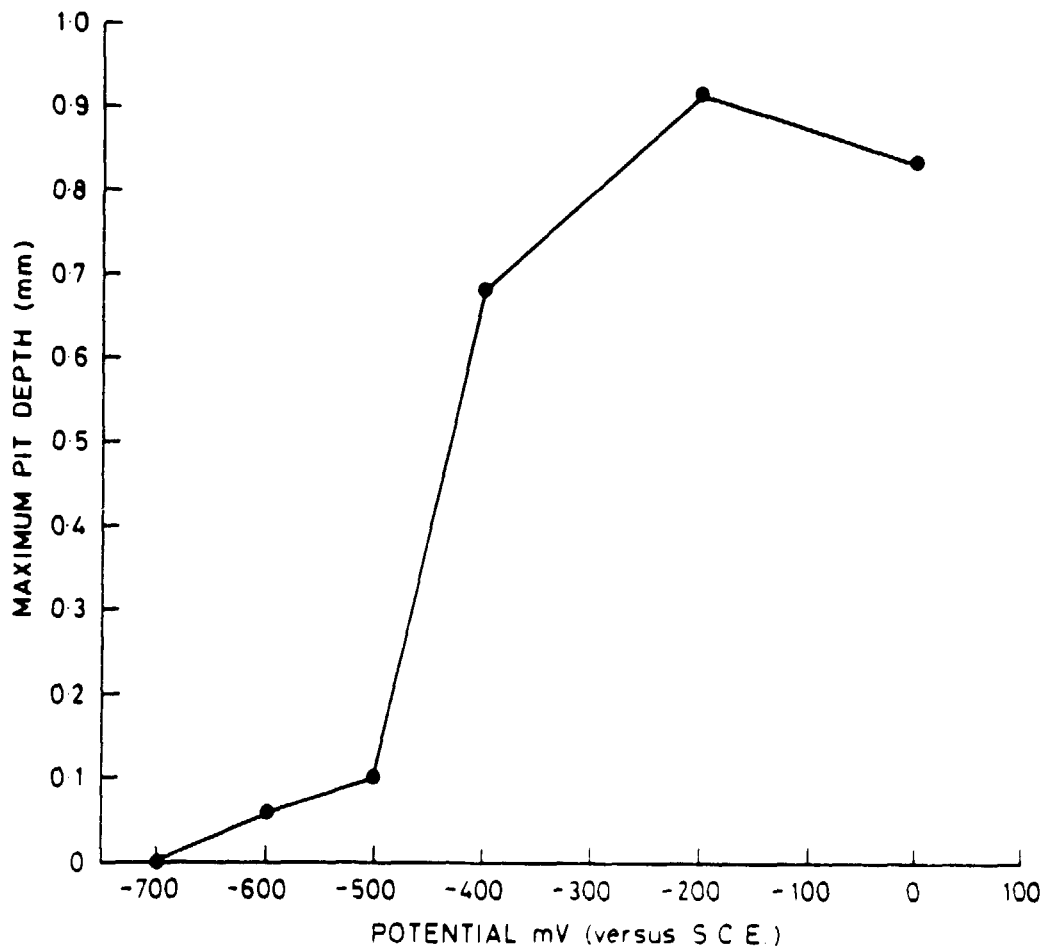


Figure 2 Variation of the maximum depth of pit penetration with electrode potential for experiments in 0.1M NaHCO_3 + 1000 ppm Cl^- solution at 90°C .

MODEL FOR OXYGEN TRANSPORT

Designs of repositories for the disposal of heat emitting wastes in granitic rock formations are typified by that developed in Sweden and described in KBS-3 [16]. Essential features are that the containers will be placed in bore-holes drilled in the floors of horizontal tunnels, and that the bore holes and tunnels will be backfilled with a low permeability material such as bentonite. In such a repository there will be three sources of oxygen or similar oxidising agents:

- (a) The air trapped in the pore space of the back-filling material.

- (b) Dissolved oxygen in the groundwater permeating the repository.
 (c) Oxidising species produced by γ -radiolysis of the groundwater.

Although the flow of water through granite may be variable because of channelling effects through cracks and fissures, the bentonite backfill will have the effect of smoothing the flow of water to the containers. It is therefore reasonable to assess the significance of oxygen transport by water flow (i.e. (b)) using an average value for water movement through granite which has been estimated to be ~ 0.2 litres $m^{-2} yr^{-1}$ [17]. Assuming this groundwater is equilibrated with air at 1 atmosphere pressure (i.e. dissolved $O_2 \sim 8$ ppm) the rate of supply of oxygen to a container of 4 m length and 1 m diameter will be 6400 ppm per year. This is equivalent to a cathodic current of about 2×10^{-7} Amps m^{-2} which is small compared to the passive leakage current from carbon steel (see later). Furthermore, because of the low permeability of the backfill, convective transport should not occur within the bore-hole, despite the heating effect of the waste [17]. Therefore calculations of the rate of transport of oxygen to the container surface need only take account of (a) and (c).

We have developed a one-dimensional model for oxygen transport under such repository conditions in which the diffusion path length 'a' is taken as the distance between the top of the container and the floor of the repository tunnel. In the model the concentration of oxygen c at any distance x from the container at time t is governed by

$$\alpha \frac{\partial C}{\partial t} = D \frac{\partial^2 C}{\partial x^2} + \alpha G R_0 \exp \left[\frac{-t}{\tau} \right] \exp \left[\frac{-x}{L} \right] \quad \text{for } 0 \leq x \leq a \quad (1)$$

where D is the intrinsic diffusion coefficient of oxygen in the backfill, R_0 the initial γ -radiation dose at the surface of the containers, τ the average disintegration constant equivalent to a mean half-life of 30 years, L the relaxation length of the backfill (0.16 m) and G the number of molecules of oxidising species produced by a 100 eV radiation dose to the groundwater. Experimental studies [3] of the effect of radiation on the rate of corrosion of carbon steel have yielded a cumulative G value, representing the maximum rate of production of all radiolytic species which are oxidising towards carbon steel, of 2.8, and this value has been used in the calculations. Finally α is a capacity factor which reflects the physical retention of the diffusing species in the porosity of the backfill and bulk chemical retention by equilibrium sorption. In this case α is taken to be equal to the porosity of the backfill (i.e. 0.33) [17].

The boundary conditions for the solution of (1) were taken as follows:

- (a) At time zero, which is taken as the time at which the repository becomes flooded, an even distribution of oxygen exists throughout the backfill pore structure. This initial concentration C_0 is taken to be 8.9×10^{-3} moles dm^{-3} , which assumes all the oxygen originally present in the pores as air, dissolves in the water which subsequently saturates the backfill.
- (b) At the container surface the flux of oxygen remains equal to the passive dissolution current (i.e. leakage current) of the carbon steel, until the concentration gradient is no longer sufficient to sustain this situation. This is described mathematically by

$$\frac{I}{4F} \leq D \frac{\partial C(o,t)}{\partial x} \quad (2)$$

- (c) The concentration of oxygen at floor of the repository tunnel (i.e.

distance 'a' from the containers) remains constant at Co. This recognises that there is a much greater volume of backfilling in the shaft, and that this may have a greater permeability permitting convective transport.

- (d) The model assumes constant temperature conditions through the backfill, and at the present stage of development the cooling of the repository is not taken into account.

Equation (1) has been solved with the above boundary conditions using a Laplace transform method. The transform is inverted numerically using Talbot's method, which involves integrating the inversion integral along the steepest descent contour of the function $g(t) = 1/t$ [18].

SENSITIVITY ANALYSIS

This model has been used to calculate the time at which the oxygen flux falls below the minimum needed to maintain passivity as a function of three key variables; the intrinsic oxygen diffusion coefficient D , the initial radiation dose rate R_0 and the passive leakage current I . The values of D investigated were 1.2×10^{-10} , 1.2×10^{-11} and $1.2 \times 10^{-12} \text{ m}^2 \text{ sec}^{-1}$, the

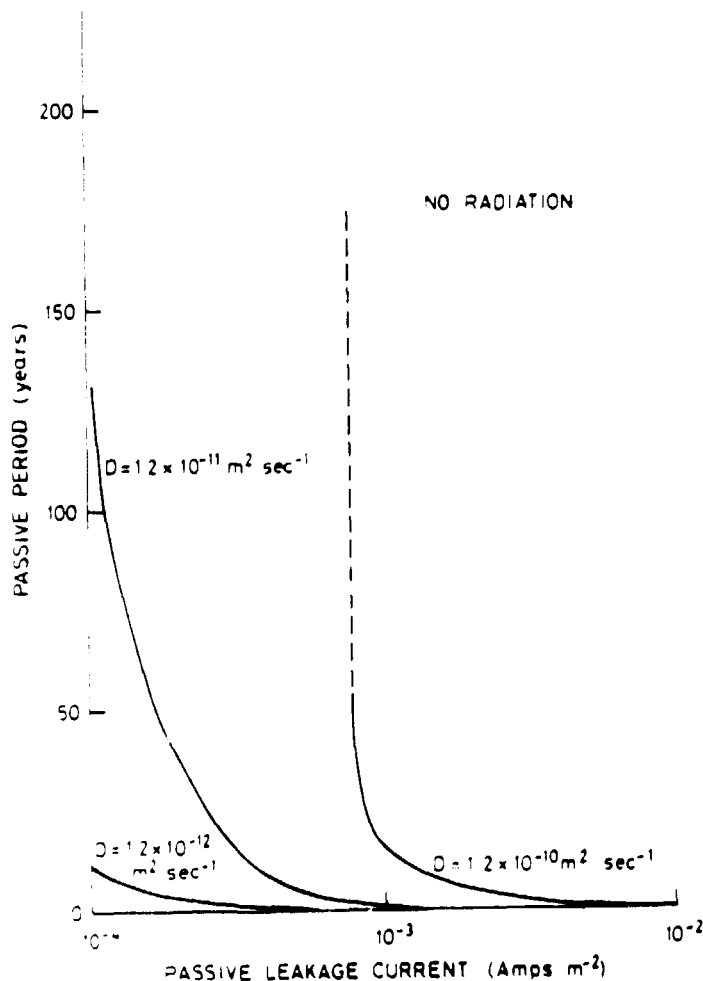


Figure 3 Passivation period as a function of leakage current and oxygen diffusion coefficient without γ -radiation.

former two being representative of O_2 diffusion coefficients through wet bentonite at $90^\circ C$ and $25^\circ C$ respectively. R_0 levels investigated were zero, 10^2 and $3.5 \times 10^3 R h^{-1}$; the latter two values representing the initial surface dose rates from carbon steel containers with wall thicknesses of approximately 250 and 100 mm, filled with 50 year old vitrified waste. These levels were selected to investigate the behaviour of containers with 180 and 30 mm corrosion allowances, since it has been estimated that a wall thickness of 70 mm will be required from considerations of mechanical strength [19]. A backfill thickness of 0.5 m was used in all the calculations.

Results for the case of a zero radiation dose indicate, as would be expected, that the passivation period of the containers falls with increasing leakage current. This period is also sensitive to the oxygen diffusion coefficient, and it is particularly significant that the calculations indicate that the containers will remain passive indefinitely, at leakage currents below $\sim 9 \times 10^{-4} A m^{-2}$ with a D of $1.2 \times 10^{-10} m^2 sec^{-1}$. This arises because, under these particular conditions, the steady state oxygen flux is sufficient to balance the passive leakage current. A similar result would have been obtained with the other D values if lower leakage currents had been investigated. Figure 4 shows that the effect of an initial radiation dose rate (i.e. R_0) of $10^2 R h^{-1}$ is to extend the passive period, particularly under conditions of slow diffusion.

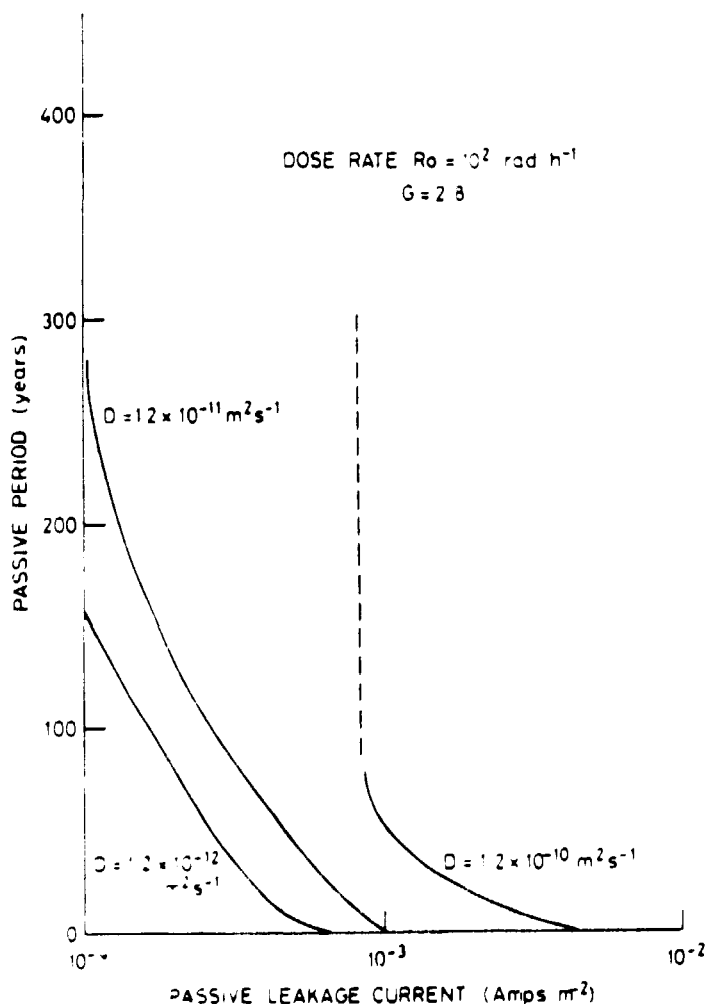


Figure 4 Passivation period as a function of leakage current and oxygen diffusion coefficient with a γ -radiation dose of $10^2 R h^{-1}$

More complex behaviour is indicated by the results for a dose rate of $3.5 \times 10^3 \text{ R h}^{-1}$ (figure 5). Here lower diffusion coefficients yield longer passivation periods, at least until the steady state oxygen flux with the highest diffusion coefficient approaches the passive leakage current below $\sim 9 \times 10^{-4} \text{ A m}^{-2}$. This anomalous behaviour would seem to be attributable to the high rate of production of oxidising radiolysis products, which are able to balance the passive leakage current, because they are slow to diffuse from the container surface. Eventually the rate of radiolysis will decrease so that the system returns to control by the diffusion of oxygen from the repository shaft. Figure 5 shows this change to normal diffusion control for $D = 1.2 \times 10^{-10} \text{ m}^2 \text{ sec}^{-1}$ at a passive leakage current of about $9 \times 10^{-4} \text{ A m}^{-2}$, but this change does not occur with the lower D values over the range of currents and times investigated.

The analysis shows that the passivation time is sensitive to any three of the parameters investigated. At a leakage current of 10^{-3} A m^{-2} and D of $1.2 \times 10^{-10} \text{ m}^2 \text{ sec}^{-1}$ the passivation time increases from 30 years at zero radiation dose to 125 years at $3.5 \times 10^3 \text{ R h}^{-1}$. This suggests that extended storage would be beneficial in reducing the period during which localised attack is possible.

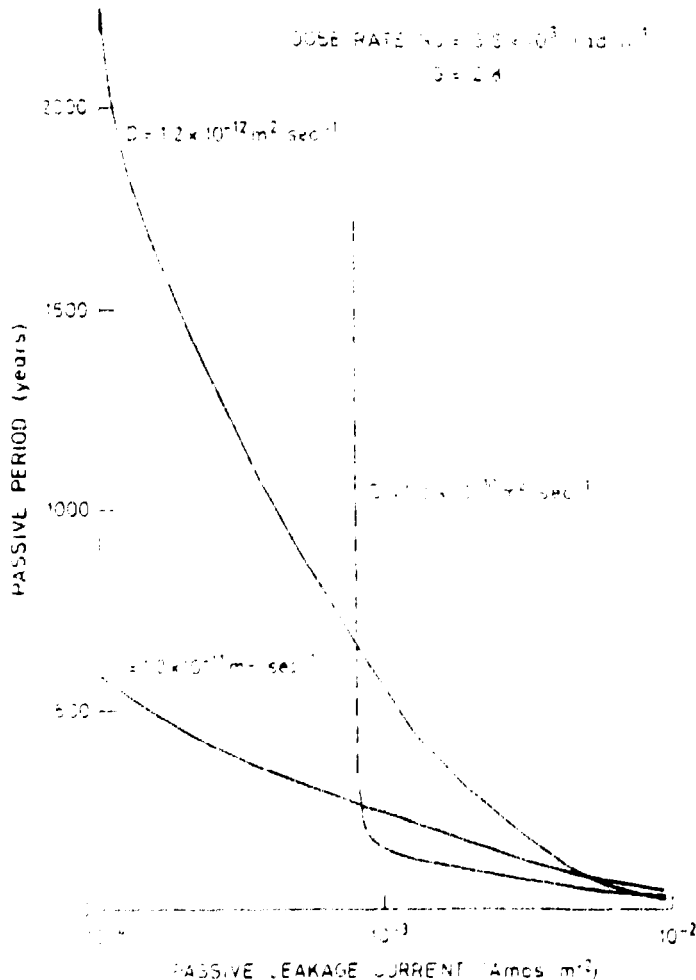


Figure 5 Passivation period as a function of leakage current and oxygen diffusion coefficient with a γ -radiation dose of $3.5 \times 10^3 \text{ R h}^{-1}$.

Interpretation of the effect of the diffusion coefficient is difficult because of the complicated behaviour predicted for the highest radiation dose rate, which was discussed above. At this stage, in what is an on-going project, the only additional observation which can be made is that the results in figure 5 may under-estimate the effect of radiation. This is because the calculations were made for constant D , whereas in practice the cooling of the repository will cause D to fall with time. This will tend to increase the passivation periods beyond those given in figure 5.

Finally the results show that if this analysis is to be applied successfully it is essential to have reliable data on the passive leakage current. This is particularly the case if D is in the region of $1.2 \times 10^{-10} \text{ m}^2 \text{ sec}^{-1}$ since a change in the leakage current from 10^{-3} to $9 \times 10^{-4} \text{ A m}^{-2}$ may change the passivation time from 30-125 years to ∞ .

ESTIMATING THE CORROSION ALLOWANCE

An indication of the benefit of estimating the passivation period can be gained using the data in figure 5. In this example the oxygen diffusion coefficient is taken to be $1.2 \times 10^{-10} \text{ m}^2 \text{ sec}^{-1}$ and the leakage current to be 10^{-3} A m^{-2} . This leakage current is considered to be reasonably conservative since results in the literature for HCO_3^- and CO_3^{2-} solutions indicate currents of $\sim 10^{-2} \text{ A m}^{-2}$ [11,20]. Furthermore the literature results are for 25°C rather than the 90°C temperature likely at least initially in a granite repository and inferred by the use of a D value of $1.2 \times 10^{-10} \text{ m}^2 \text{ sec}^{-1}$. On the other hand, however, the literature data were obtained from short term electrochemical tests, and it would be expected that the leakage current would have fallen to some extent with time. In fact one important requirement for applying this method for evaluating corrosion allowances is the provision of reliable data on the passive leakage currents of carbon steel under relevant environmental conditions.

Using the values specified above, figure 5 indicates a passivation period of 125 years. Assuming that localised corrosion occurs during this period the maximum depth of penetration can be estimated from the expression [3]

$$P = 8.35 t^{0.46} \quad (3)$$

where P is in mm and t in years. This predicts a maximum localised corrosion penetration of 77 mm.

Beyond the first 125 years the containers will be subject to general corrosion, and in this case experimental measurements have indicated that the maximum rate of attack will be $\sim 10 \mu\text{m/yr}$ [3]. This infers an additional corrosion allowance for a 1000 year container life of ~ 9 mm, so that the total allowance is 86 mm. This should be compared with an allowance of 200 mm if it had been assumed that localised corrosion could occur throughout the container life.

It must be emphasised that the above has only been presented by way of an example of the potential benefit to be gained by estimating the period during which localised corrosion may occur. A reliable estimate must await refinement of the model to take account of the change in repository temperature with time, and better estimates of the passive leakage currents under repository conditions. However, the example illustrates that this approach may reduce the corrosion allowance by the order of 50%, which would be beneficial not only in reducing material costs but also in simplifying container manufacture and seal welding. It will also reduce the weight of the containers which has implications on handling and transportation problems underground.

4. R.N. Parkins, Stress Corrosion Cracking Tests on Electron Beam Welded Carbon Steel Specimens in Carbonate-Bicarbonate Solution, AERE-G3583 (1985).
5. D. Hardie, An Assessment of the Risk of Embrittlement of a Steel Container by Hydrogen Picked up from the Ocean Bed, AERE-G3587 (1985).
6. G.P. Marsh, K.J. Taylor, I.D. Bland, C. Westcott, P.W. Tasker and S.M. Sharland, Evaluation of the Localised Corrosion of Carbon Steel Overpacks for Nuclear Waste Disposal in Granite Environments, MRS Conference on Radioactive Waste Management, Stockholm, September 1985, editor L. Werme.
7. S.M. Sharland, A Mathematical Model of Crevice and Pitting Corrosion, TP-1183 (1986).
8. M. Pourbaix, Corrosion, 26, No. 10, (October 1970, 431-438).
9. E. Deltombe and M. Pourbaix, CEBELCOR Rapport Technique 8, Centre Belge d'Etude de la Corrosion.
10. J.M. Sutcliffe, R.R. Fessler, W.K. Boyd and R.N. Parkins, Corrosion, 28, No. 8, 313-320 (1972).
11. J.G.N. Thomas, T.J. Nurse and R. Walker, Br. Corros. J., 5, 87-92, (March 1970).
12. Localized Corrosion, NACE-3, edited by R.W. Staehle, B.F. Brown, J. Kruger, A. Agrawal, (published by National Association of Corrosion Engineers).
13. M. Pourbaix, The Theory of Stress Corrosion Cracking in Alloys, p. 17, edited by J.C. Scully (published by NATO Scientific Affairs Division, Brussels) 1971.
14. B.F. Brown, C.T. Fujii and E.P. Dahlberg, J. of Electrochem. Soc., 116, No. 2, pp. 218-219 (1969).
15. G. Sandoz, C.T. Fujii and B.F. Brown, Corrosion Science, 10, No. 12, pp. 839-846 (1970).
16. Final Storage of Spent Nuclear Fuel - KBS 3, I - General, SKBF/KBS Report, eds. E. Svenke and L.B. Nilsson (1983).
17. L. Ekbohm, Copper as Canister Material for Unreprocessed Nuclear Waste - Evaluation with Respect to Corrosion, KBS-TR-90, Final Report 1978-03-31.
18. A. Talbot, The Accurate Numerical Inversion of Laplace Transforms, J. Inst. Maths. Applics., 23, 97 (1979).
19. G.P. Marsh, G. Pinard-Legry, E. Smailos, F. Casteels, K. Vu Quang, J. Cripps and B. Haijtink, HLW Container Corrosion and Design, Proceedings of 2nd European Community Conference on Radioactive Waste Management and Disposal, Luxembourg, p. 314, (1985).
20. G.K Glass, Corrosion Science, 26, No. 6, pp 441-454 (1986).

CONCLUSION

1. A mechanistically based approach has been developed for estimating the maximum period during which carbon steel containers for HLW may be subject to localised corrosion in a geological repository.
2. A mathematical model is under development for estimating the maximum period for localised corrosion based on the KBS design for a granite repository using bentonite as a backfill material.
3. At present the model works for constant temperature conditions but further development is underway to include the temperature transients which will occur under repository conditions.
4. A sensitivity analysis using the existing constant temperature model has shown that the estimated localised corrosion period increases significantly with radiation dose rate.
5. The localised corrosion period is also strongly dependent on the oxygen diffusion coefficient. Without radiation the localised corrosion period falls as the diffusion coefficient is reduced, but at a dose rate of $3.5 \times 10^3 \text{ R h}^{-1}$ this trend is reversed. This has been attributed to the retention of oxidising radiolytic specimens at the container surface under low diffusivity conditions.
6. The localised corrosion period is also critically dependent on the passive film leakage current, and more accurate long term data on this parameter are needed before reliable estimates can be made.
7. A demonstration calculation using existing data has shown that the corrosion allowance specified for carbon steel containers may be reduced by the order of 50% if the above model is used to estimate the localised corrosion period rather than assuming such attack will continue throughout the container life. This reduction has potential benefits for the manufacture, seal welding and underground handling of carbon steel containers.

ACKNOWLEDGEMENTS

The sponsorship of SKB (Sweden) for the theoretical analysis of oxygen transport is gratefully acknowledged.

REFERENCES

1. G.P. Marsh, Nucl. Energy, 21, No. 4, 253 (1982).
2. G.P. Marsh, I.D. Bland, J.A. Desport, C.C. Naish, C. Westcott and K.J. Taylor, European Appl. Res. Rept. - Nucl. Sci. Technol., 5, No. 2, 223 (1983).
3. G.P. Marsh, I.D. Bland, K.J. Taylor, S.M. Sharland and P. Tasker, An Assessment of Carbon Steel Overpacks for Radioactive Waste Disposal, Report EUR 10437 EN, published by the Commission of the European Communities, (1986).

List of SKB reports

Annual Reports

1977-78

TR 121

KBS Technical Reports 1 - 120.

Summaries. Stockholm, May 1979.

1979

TR 79-28

The KBS Annual Report 1979.

KBS Technical Reports 79-01 - 79-27.

Summaries. Stockholm, March 1980.

1980

TR 80-26

The KBS Annual Report 1980.

KBS Technical Reports 80-01 - 80-25.

Summaries. Stockholm, March 1981.

1981

TR 81-17

The KBS Annual Report 1981.

KBS Technical Reports 81-01 - 81-16.

Summaries. Stockholm, April 1982.

1982

TR 82-28

The KBS Annual Report 1982.

KBS Technical Reports 82-01 - 82-27.

Summaries. Stockholm, July 1982.

1983

TR 83-77

The KBS Annual Report 1983.

KBS Technical Reports 83-01 - 83-76

Summaries. Stockholm, June 1984.

1984

TR 85-01

Annual Research and Development Report 1984

Including Summaries of Technical Reports Issued during 1984. (Technical Reports 84-01-84-19)

Stockholm June 1985.

1985

TR 85-20

Annual Research and Development Report 1985

Including Summaries of Technical Reports Issued during 1985. (Technical Reports 85-01-85-19)

Stockholm May 1986.

1986

TR86-31

SKB Annual Report 1986

Including Summaries of Technical Reports Issued during 1986

Stockholm, May 1987

Technical Reports

1987

TR 87-01

Radar measurements performed at the Klipperås study site

Seje Carlsten, Olle Olsson, Stefan S hlstedt, Leif Stenberg

Swedish Geological Co, Uppsala/Lule 

February 1987

TR 87-02

Fuel rod D07/B15 from Ringhals 2 PWR: Source material for corrosion/leach tests in groundwater

Fuel rod/pellet characterization program part one

Roy Forsyth

Studsvik Energiteknik AB, Nyk ping

March 1987

TR 87-03

Calculations on HYDROCOIN level 1 using the GWHRT flow model

Case 1 Transient flow of water from a borehole penetrating a confined aquifer

Case 3 Saturated-unsaturated flow through a layered sequence of sedimentary rocks

Case 4 Transient thermal convection in a saturated medium

Roger Thunvik, Royal Institute of Technology, Stockholm

March 1987

TR 87-04

Calculations on HYDROCOIN level 2, case 1 using the GWHRT flow model

Thermal convection and conduction around a field heat transfer experiment

Roger Thunvik

Royal Institute of Technology, Stockholm

March 1987

TR 87-05

Applications of stochastic models to solute transport in fractured rocks

Lynn W Gelhar

Massachusetts Institute of Technology

January 1987

TR 87-06

Some properties of a channeling model of fracture flow

Y W Tsang, C F Tsang, I Neretnieks
Royal Institute of Technology, Stockholm
December 1986

TR 87-07

Deep groundwater chemistry

Peter Wikberg, Karin Axelsen, Folke Fredlund
Royal Institute of Technology, Stockholm
June 1987

TR 87-08

An approach for evaluating the general and localized corrosion of carbon steel containers for nuclear waste disposal

GP March, KJ Taylor, SM Sharland, PW Tasker
Harwell Laboratory, Oxfordshire
June 1987

TR 87-09

Piping and erosion phenomena in soft clay gels

Roland Pusch, Mikael Erlström,
Lennart Börgesson
Swedish Geological Co, Lund
May 1987

TR 87-10

Outline of models of water and gas flow through smectite clay buffers

Roland Pusch, Harald Hökmark,
Lennart Börgesson
Swedish Geological Co, Lund
June 1987

TR 87-11

Modelling of crustal rock mechanics for radioactive waste storage in Fennoscandia - Problem definition

Ove Stephansson
University of Luleå
May 1987

TR 87-12

Study of groundwater colloids and their ability to transport radionuclides

Kåre Tjus* and Peter Wikberg**
*Institute for Surface Chemistry, Stockholm
**Royal Institute of Technology, Inorganic
Chemistry Stockholm
March 1987

ISSN 0348-7504

© All Rights Reserved 2007