

FAL-9127208

ISSN 0029-3865



**CBPF**-CENTRO BRASILEIRO DE PESQUISAS FÍSICAS

---

---

## Notas de Física

CBPF-NF-001/91

MAGNETIC FIELD AND TEMPERATURE DEPENDENCE OF THE FLUORESCENCE  
LIFETIME OF  $CR^{3+}$  IN  $GdAlO_3$

by

J.S. HELMAN, A.O. CARIDE, H.C. BASSO, M.C. TERRILE and  
R.A. CARVALHO

RIO DE JANEIRO

1991

**NOTAS DE FÍSICA** é uma pré-publicação de trabalho original em Física

**NOTAS DE FÍSICA** is a preprint of original works unpublished in Physics

Pedidos de cópias desta publicação devem ser enviados aos autores ou a:

Requests for copies of these reports should be addressed to:

Centro Brasileiro de Pesquisas Físicas  
Área de Publicações  
Rua Dr. Xavier Sigaud, 150 - 4º andar  
22.290 - Rio de Janeiro, RJ  
BRASIL

CBPF-NF-001/91

MAGNETIC FIELD AND TEMPERATURE DEPENDENCE OF THE FLUORESCENCE  
LIFETIME OF  $CR^{3+}$  IN  $GdAlO_3$

by

J.S. HELMAN<sup>1</sup>, A.O. CARIDE<sup>1</sup>, H.C. BASSO<sup>2</sup>, M.C. TERRILE<sup>2</sup> and  
R.A. CARVALHO<sup>2</sup>

<sup>1</sup>Centro Brasileiro de Pesquisas Físicas - CBPF/CNPq  
Rua Dr. Xavier Sigaud, 150  
22290 - Rio de Janeiro, RJ - Brasil

<sup>2</sup>Instituto de Física e Química de São Carlos  
Universidade de São Paulo  
13560 - São Carlos, SP - Brasil

The fluorescence lifetime of  $\text{Cr}^{3+}$  in  $\text{GdAlO}_3$  was measured in the range 1.8 - 4.2 K in magnetic fields up to 6 T. The results show a remarkable dependence of the transition probabilities on magnetic order. A model based on the exchange interaction between  $\text{Cr}^{3+}$  in highly excited states and the  $\text{Gd}^{3+}$  ions is proposed.

PACS: 78.20.Ls, 78.55.Hx, 75.30.Hx

KEY WORDS: Luminescence, Magneto-optical effects.

A handwritten signature in black ink, appearing to be 'P. Anis', located in the lower-left quadrant of the page.

## INTRODUCTION

The optical and magnetic properties of the antiferromagnet  $\text{GdAlO}_3$  with  $\text{Cr}^{3+}$  impurities substituting for  $\text{Al}^{3+}$  have been extensively studied both theoretically and experimentally.<sup>1-13</sup> In particular the fluorescence lifetime was measured by Ohlman et al<sup>1</sup> for some temperatures above and below the Neel point and systematically by Aegerter et al<sup>8</sup> throughout the antiferromagnetic phase. A sharp shortening of the lifetime with the onset of antiferromagnetic order was observed. The origin of this strong dependence on magnetic order remained, however, unexplained and motivated the present additional measurements of fluorescence lifetime with applied magnetic field. The measurements were performed at low temperatures (1.8 - 4.2 K) in the presence of external fields up to 6 T.

Electric dipole transitions between the  ${}^4A_2$  ground state and the first excited state  ${}^2E$  of  $\text{Cr}^{3+}$  are spin and parity forbidden. We show here that the combined action of the spin orbit interaction and the exchange coupling of  $\text{Cr}^{3+}$  in highly excited states with the neighboring  $\text{Gd}^{3+}$  ions provides a mechanism that makes possible those transitions and accounts for their dependence on the magnetic order of the matrix.

## EXPERIMENTAL

A  $\text{GdAlO}_3$  single crystal<sup>14,15</sup> having a nominal  $\text{Cr}^{3+}$  concentration of 0.1%, was placed in a He bath inside a NbTi-superconducting split coil from IGC. The crystal was oriented with the [100] (easy axis) or [001]

directions along the magnetic field. Fluorescence was excited using a Spectra-Physics CW argon laser in multiline emission. The laser light, propagating along the magnetic field, was chopped at 3 Hz by an Ealing electromagnetic shutter. The fluorescence was measured in the direction perpendicular to the magnetic field with a 0.5 m Jarrel-Ash monochromator, followed by an RCA 4832 photomultiplier and an EGG model 113 pre-amplifier.

Two different setups were used to measure the fluorescence lifetime. In the first, a PAR Signal Averager, connected to a microcomputer and synchronized to the shutter, recorded the time evolution of the fluorescence signal (measured at the peak of each line). The signal intensity vs time could be adjusted by a single exponential decay in every case independent of the fluorescence line, the temperature and the magnetic field. It was verified that the four fluorescence lines had the same decay time. Taking advantage of this fact, and that the wave number of the fluorescence line at  $13754 \text{ cm}^{-1}$  is practically independent of the magnetic field<sup>11</sup>, a second setup was devised in which a boxcar integrator replaced the signal averager. It sampled the intensity of this line at two different times,  $I(t)$  and  $I(t+T)$ , with constant delay time  $T = 10 \text{ ns}$ , while the magnetic field was being swept continuously. The decay rate is given by  $W = \ln(I(t)/I(t+T))/T$ . Measurements were performed at temperatures between 1.8 K and 4.2 K and magnetic fields in the range 0-6 T. The results are shown in Figs. 2-4.  $W$  decreases with increasing magnetic field and tends to a constant value  $W_0 \approx 40 \text{ s}^{-1}$  as the magnetization of the sample saturates. The nature of the magnetic order independent background decay  $W_0$  was not

identified.

## MODEL

The fluorescence life time  $\tau$  is related to the oscillator strength for electric dipole transitions  $f$  by<sup>16</sup>

$$f\tau = 1.5 \cdot 10^4 \frac{\lambda_0^2}{[(n^2+2)/3]^2 n} \quad (1)$$

in SI units, where  $\lambda_0$  is the wavelength in vacuum and  $n$  the refractive index. In the case of  $\text{Cr}^{3+}$  in  $\text{GdAlO}_3$  is  $\lambda_0 \cong 7260 \text{ \AA}$  and  $n \cong 2.05$  yielding  $f\tau = 9.0 \cdot 10^{-10}$  sec. For  $\text{Cr}^{3+}$  into  $\text{Al}_2\text{O}_3$  (ruby), the product  $f\tau$  is roughly the same and, since its fluorescence life time is 4 ms, we get  $f_{\text{Ruby}} = 2.5 \cdot 10^{-7}$ . Theoretically, the oscillator strength is given by

$$f = \sum_{^4A_2} \frac{2m\omega_0}{3h} \left| \langle ^4A_2 | \sum_1^3 r_1 | ^2E \rangle \right|^2 \quad (2)$$

where  $r_1$  are the coordinates of the three d-electrons of  $\text{Cr}^{+3}$  and the sum is over the  $^4A_2$  multiplet.  $|^4A_2\rangle$  and  $|^2E\rangle$  indicate the perturbed ground and first excited state of  $\text{Cr}^{+3}$  in the cubic crystal field.  $m$  is the electron mass,  $h$  Planck's constant and  $\omega_0$  the light frequency. Transitions between the unperturbed states are both spin and parity forbidden. In the case of ruby, for instance, the prohibition is lifted by the combined action of the spin-orbit interaction and the hemihedral part of the trigonal field.<sup>17</sup>

In  $\text{GdAlO}_3$  the  $\text{Cr}^{+3}$  impurities occupy sites with *spatial* inversion symmetry. Inversion symmetry, however, is broken by the Gd spins and thus the oscillator strength depends strongly on the magnetic order of the neighboring Gd ions. We propose that the combined action of the spin orbit interaction and the exchange coupling of Cr with the neighboring Gd ions are responsible for the lifting of the spin and parity prohibitions, respectively.

We will consider in detail the dependence of the oscillator strength on the magnetic order, while the values of the matrix elements involved will only be estimated in order of magnitude.

The exchange interaction between Cr and its neighboring Gd ions can be phenomenologically written in the form

$$V_{ex} = \sum_{i,j} J(|r_i - R_j|) s_i \cdot S_j \quad (3)$$

where the exchange coupling  $J$  is assumed to be only a function of the distance between a Cr d-electron at position  $r_i$  and the Gd nucleus at  $R_j$ .  $s_i$  is the spin operator of the electron at  $r_i$  and  $S_j$  is the total spin operator of the Gd ion in its ground state ( $S = 7/2$ ). The sum over  $i$  runs over the three d-electrons and the sum over  $j$  runs over the eight nearest neighbor Gd ions.



The lowest order term in a Taylor development of  $V_{\text{ex}}$  which gives a contribution to the decay rate is

$$V'_{\text{ex}} = \frac{1}{6} \sum_i \left( \frac{\partial^3 V_{\text{ex}}}{\partial x_i \partial y_i \partial z_i} \right)_0 x_i y_i z_i. \quad (4)$$

This has  $A_{2u}$  symmetry in the cubic group and lifts the parity prohibition.

Using (3)

$$V'_{\text{ex}} = C \sum_{\alpha} \sum_j R_j^x R_j^y R_j^z S_j^{\alpha} \sum_i x_i y_i z_i s_i^{\alpha} \quad (5)$$

with

$$C = -\frac{1}{6R^3} \left( \frac{\partial^3 J}{\partial R^3} - \frac{3}{R} \frac{\partial^2 J}{\partial R^2} + \frac{3}{R^2} \frac{\partial J}{\partial R} \right) \quad \text{at } R = R_0, \quad (6)$$

where  $R_0 = 3.23 \text{ \AA}$  is the Cr-Gd distance. Cubic symmetry ensures that the sum over the modulus square of the matrix elements of  $s_i^{\alpha}$  between the intervening states (which below we generically call  $|M|^2$ , Eq. 24) will be independent of  $\alpha$ . Thus, in calculating the transition rate we will be concerned with the thermodynamic average

$$D = \left\langle \left| \sum_{\alpha} \sum_j R_j^x R_j^y R_j^z S_j^{\alpha} \right|^2 \right\rangle \quad (7)$$

namely,

$$D = \sum_j \sum_{j'} \sum_{\alpha} \sum_{\alpha'} R_j^x R_j^y R_j^z R_{j'}^x R_{j'}^y R_{j'}^z \langle S_j^{\alpha} S_{j'}^{\alpha'} \rangle. \quad (8)$$

Neglecting correlations between different components of the Gd spins

$$D = \sum_j \sum_{j'} R_j^x R_j^y R_j^z R_{j'}^x R_{j'}^y R_{j'}^z \langle S_j \cdot S_{j'} \rangle. \quad (9)$$

We shall write

$$S_j = \langle S_j \rangle + Y_j \quad (10)$$

where  $\langle S_j \rangle$  is the thermodynamic average of the spin operator  $S_j$  and  $Y_j = S_j - \langle S_j \rangle$  the spin fluctuation operator. Note that  $\langle Y_j \rangle = 0$  and  $\langle Y_j^2 \rangle = S(S+1) - \langle S_j \rangle^2$ . Replacing (10) into (9) we have

$$D = I_0 + I_1 + I_2 \quad (11)$$

where

$$I_0 = \left( \sum_j R_j^x R_j^y R_j^z \langle S_j \rangle \right)^2 \quad (12)$$

$$I_1 = \sum_j \left( R_j^x R_j^y R_j^z \right)^2 \left[ S(S+1) - \langle S_j \rangle^2 \right] \quad (13)$$

$$I_2 = \sum_{j \neq j'} \sum R_j^x R_j^y R_j^z R_{j'}^x R_{j'}^y R_{j'}^z \langle Y_j \cdot Y_{j'} \rangle. \quad (14)$$

We note that  $I_0$  vanishes for a ferromagnetic alignment while it is maximum for saturated two sublattice antiferromagnetic order. Since  $(R_j^x R_j^y R_j^z)^2 = q$ , with  $q = R_0^6/27$ , the term  $I_1$  gives an important contribution even for fully disordered Gd spins. In the following we will neglect the correlation between the fluctuations of next nearest neighbor Gd spins. The correlation between the fluctuations of nearest neighbor Gd spins will be described by the parameter  $p$  defined by

$$\langle Y_j \cdot Y_{j'} \rangle = \left( S(S+1) - \langle S_j \rangle^2 \right)^{1/2} \left( S(S+1) - \langle S_{j'} \rangle^2 \right)^{1/2} p. \quad (15)$$

-8-

$p$  varies in the range  $-1 < p < 1$ .  $p > 0$  ( $< 0$ ) means ferromagnetic (antiferromagnetic) correlation. We note that  $R_j^x R_j^y R_{j'}^z R_{j'}^x, R_j^y R_j^z, = -q$  for nearest neighbor  $j, j'$ . Next, we write explicit expressions for  $D$  corresponding to particular magnetic configurations. We obtain from Eqs. (11-15),  $D = 64qS^2F$  where

$$F = \sigma^2 + (1 + 1/S - \sigma^2)(1 - 3p)/8 \quad (16)$$

for antiferromagnetic order (AF) with reduced sublattice magnetization  $\sigma(T) = \langle S_j \rangle_T / S$ ;

$$F = (1 + 1/S - m^2)(1 - 3p)/8 \quad (17)$$

in the paramagnetic region (PM) where  $m(T, H) = \langle S_j \rangle_{T, H} / S$  is the reduced magnetization;

$$F = (\sigma_A + \sigma_B)^2/4 + \left[ 1 + 1/S - (\sigma_A^2 + \sigma_B^2)/2 \right] / 8 \quad (18)$$

$$- (3p/8) \left[ (1 + 1/S - \sigma_A^2)(1 + 1/S - \sigma_B^2) \right]^{1/2}$$

for an antiferromagnet in an external field applied along the easy direction.  $\sigma_{A, B}(T, H)$  are the reduced sublattice magnetizations;

$$F = (\sigma \sin\varphi)^2 + (1 + 1/S - \sigma^2)(1 - 3p)/8 \quad (19)$$

$$F = (\sigma \cos\varphi)^2 + (1 + 1/S - \sigma^2)(1 - 3p)/8 \quad (19')$$

for an antiferromagnet in the spin-flop (FL) region,  $\sigma(T)$  is the reduced sublattice magnetization and  $\varphi$  its angle with respect to the easy direction. Eqs. (19) and (19') apply for H parallel and perpendicular to the easy direction respectively.

The order of magnitude of the parameter C given by (6) can be estimated by assuming a form for the function J(R). A tractable and reasonable form is<sup>13</sup>

$$J(R) = J_0 e^{-R/\rho} \quad (20)$$


where  $\rho$  is of the order of the radius of the Cr ion. Thus

$$C = \frac{J_0 e^{-R_0/\rho}}{6R_0^3 \rho^3} \left( 1 + \frac{3\rho}{R_0} + \frac{3\rho^2}{R_0^2} \right). \quad (21)$$


There are only two possibilities of fluorescent decay mediated by  $V'_{ex}$ , Fig 1 (As it is shown below  $V'_{ex}$  is of the order of  $KvF \cong 450 \text{ cm}^{-1}$ ):

-10-


I)

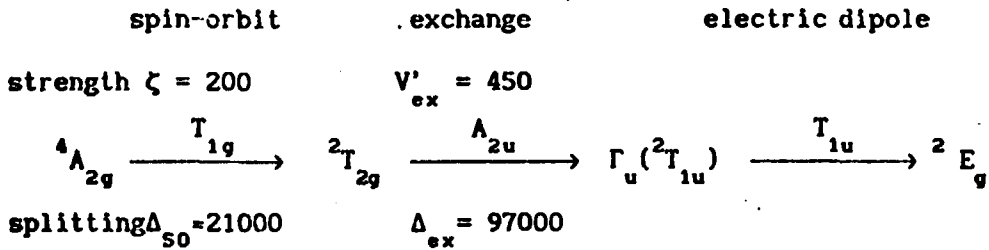

II)

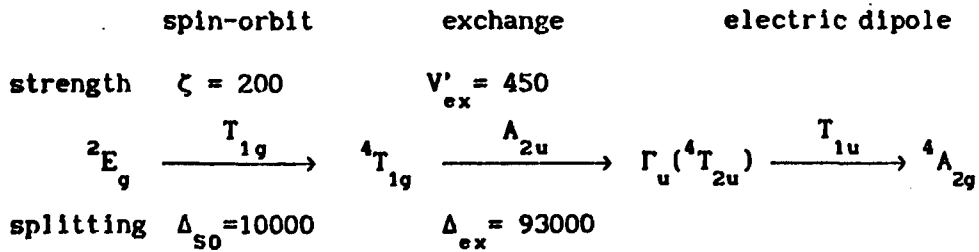

In ruby the dominant decay process involves<sup>17</sup>:

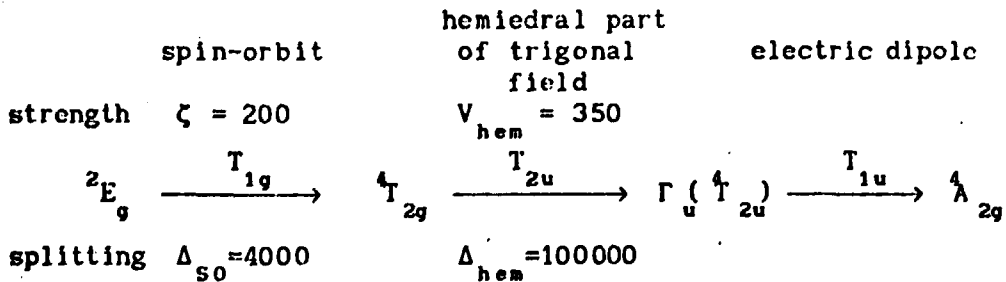

In view of the smaller denominators the second process dominates and we will restrict to it. Thus we can write

$$|\langle {}^4T_{1g} | V'_{ex} | \Gamma_u({}^4T_{2u}) \rangle|^2 = K^2 F \quad (22)$$

where

$$K = 0.9 J_0 e^{-R_0/\rho} \left( 1 + \frac{3\rho}{R_0} + \frac{3\rho^2}{R_0^2} \right) |M| \quad (23)$$

with

$$M = \langle {}^4T_{1g} | \sum_i x_i y_i z_i s_i^\alpha | \Gamma_u ({}^4T_{2u}) \rangle / \rho^3. \quad (24)$$

For instance, if we put  $\rho = 1 \text{ \AA}$  and  $M = 1$  then  $K = 0.08 J_0$ .

It follows from Eq.(2) that in order of magnitude the oscillator strength is proportional to the factors  $(\zeta/\Delta_{SO})^2$  and  $(V_{hem}/\Delta_{hem})^2$  responsible for the lifting of the spin and parity prohibitions, thus we write

$$f_{\text{Ruby}} = G \left( \frac{\zeta}{\Delta_{SO}} \right)^2 \left( \frac{V_{hem}}{\Delta_{hem}} \right)^2. \quad (25)$$

where  $G = 8.16$  is adjusted to reproduce the value of the oscillator strength of ruby. We shall assume that the same constant  $G$  applies to Cr into  $\text{GdAlO}_3$ . Thus, with values corresponding to process II above, we have

$$f = G \left( \frac{200}{10000} \right)^2 \left( \frac{K}{93000} \right)^2 F \quad (26)$$

and from (1), the decay rate induced by the spin disorder is

$$1/\tau = 4.19 \cdot 10^{-4} K^2 F. \quad (27)$$

We shall denote by  $W_0$  the decay rate induced by other mechanisms independent of the magnetic order of the matrix. Thus, to compare with experiment, we add to  $1/\tau$  a constant background decay rate  $W_0$ , namely,

$$W = W_0 + 1/\tau \quad (28)$$

#### COMPARISON WITH EXPERIMENT

Fig 2 shows the decay rate as a function of temperature in the absence of magnetic field. The experimental values were taken from Ref. 8. The theoretical result (full line) was obtained from Eq. (28) using the expression for  $F$  given by (16) with values of  $\sigma(T)$  calculated within the molecular field approximation.<sup>5</sup> The fitting yields  $p = -0.2$ ,  $K = 463 \text{ cm}^{-1}$  and  $W_0 = 40 \text{ s}^{-1}$ . If we assume  $\rho = 1 \text{ \AA}$  and  $|M| = 1$ , this yields  $J_0 = 5.8 \cdot 10^3 \text{ cm}^{-1} = 0.7 \text{ eV}$ . This value of  $J_0$  is compatible with that previously found for the lower states of Cr in  $\text{GdAlO}_3$ .<sup>13</sup>

Fig 3 shows the decay rate as a function of the magnetic field (perpendicular to the easy axis) for  $T = 4.2 \text{ K}$  (paramagnetic region) and  $T = 2 \text{ K}$  (below the Neel temperature). The theoretical results for  $T = 4 \text{ K}$  were obtained from Eq. (28) with  $F$  given by Eq. (17). Those for  $T = 2 \text{ K}$  were calculated using  $F$  given by Eq. (19') in the AF region ( $H < 3 \text{ T}$ ) and by Eq. (17) in the PM region ( $H > 3 \text{ T}$ ). A smooth interpolation was made in the



transition region. The same values for  $p$ ,  $K$  and  $W_0$  found above were used. The values of  $\sigma$ ,  $\varphi$  and  $m$  were calculated within the molecular field approximation.<sup>5</sup>

Fig 4 shows the decay rate as a function of the magnetic field (parallel to the easy axis) for  $T = 1.8$  K. The theoretical results were obtained from Eq.(28) with  $F$  given by Eq.(18) in the AF region ( $H < 1.2$  T), Eq.(19) in the SF region ( $1.2$  T  $< H < 3$  T) and Eq.(17) in the PM region ( $H > 3$  T). Smooth interpolations were made in the transition regions. Again the same values for  $p$ ,  $K$  and  $W_0$  found above were used here. The values of  $\sigma_A$ ,  $\sigma_B$ ,  $\sigma$ ,  $\varphi$  and  $m$  were calculated within the molecular field theory.<sup>5</sup> The theory predicts a discontinuity in the decay rate at the AM-FL transition. This was not shown, however, by our experimental results possibly because the noise level was not low enough or a small misalignment of the crystal easy axis broadened the AM-FL discontinuity.

## SUMMARY AND DISCUSSION

We propose a model which accounts for the strong dependence on magnetic order of the luminescence decay rate of  $\text{Cr}^{3+}$  in the two-sublattice antiferromagnet  $\text{GdAlO}_3$ . The luminescent transition is in principle spin and parity forbidden. The spin orbit interaction lifts the spin prohibition. The different orientations of the spins of the eight neighboring Gd ions break the inversion symmetry of the crystal field potential via the

exchange coupling between the 3d-electrons of Cr and the 4f-electrons of the Gd ions, thus lifting the parity prohibition. The model yields the dependence of the decay rate in terms of the parameters which describe the magnetic order of the matrix in its different phases. Cr in its excited state  ${}^2E$  does not influence the magnetic order of the neighboring Gd spins<sup>9,11</sup> which may thus be accurately described within the molecular field approximation with coupling constants appropriate to the pure matrix.<sup>5</sup> The magnitude of the electric dipole transition matrix elements involved are borrowed from the similar case of ruby. The theory still involves three adjustable parameters which were determined from the experimental data (Figs 2-4):

1) The background constant decay rate  $W_0 = 40 \text{ s}^{-1}$ , which is most probably induced by the presence of other impurities or defects.

2) The correlation between fluctuations of the Gd spins  $p = -0.2$ , whose evaluation is beyond the molecular field approximation. Although this parameter should be temperature dependent it was considered to be constant within the limited temperature range of the experiments. An independent value of this correlation, obtained from the splitting of the luminescence lines at  $T = 1.5 \text{ K}$  in the spin-flop phase yielded  $p = -0.3$ .<sup>12</sup>

3) The parameter  $K = 463 \text{ cm}^{-1}$  is basically connected to the derivatives of the exchange integrals between the 3d-electrons of Cr in the highly excited states  ${}^4T_{1g}$  and the f-electrons of Gd. We modelled this interaction in the most simple possible way (following Ref. 13). This permits analytical calculations and, in order of magnitude, we arrive at a

value for the pre-exponential factor of Eq.(20) of  $J_0 = 0.7$  eV which is consistent with the 0.85 eV obtained for that of the direct exchange of Cr in the lower states  ${}^2E_g$  and  ${}^4A_{2g}$ .<sup>13</sup>

#### ACKNOWLEDGMENTS

We thank Profs. W. Baltensperger, S. I. Zanette, H. Panepucci and Mr. R. C. Paschoal for fruitful discussions, and Prof. Glauius Oliva for assistance with the crystal orientation.

We thank the Fundação de Amparo a Pesquisa do Estado de São Paulo (FAPESP) and Financiadora de Estudos e Projetos (FINEP), Brazil, for financial support.

## FIGURE CAPTIONS

Fig 1.- Energy level scheme for  $\text{Cr}^{+3}$  showing the intervening mechanisms in the fluorescence of ruby and Cr doped  $\text{GdAlO}_3$ .

Fig 2.- Temperature dependence of the decay rate in the absence of magnetic field. Experimental data taken from Fig 6 of Ref. 8 (O). Theory: full line.

Fig. 3.- Fluorescence decay rate vs magnetic field perpendicular to the easy axis. Experiment ( $\Delta$ ) at 2 K, (O) at 4.2 K; theory: full lines.

Fig 4.- Fluorescence decay rate vs magnetic field (parallel to easy axis) at 1.8 K. Experiment ( $\Delta$ ). Theory: full line.

-17-

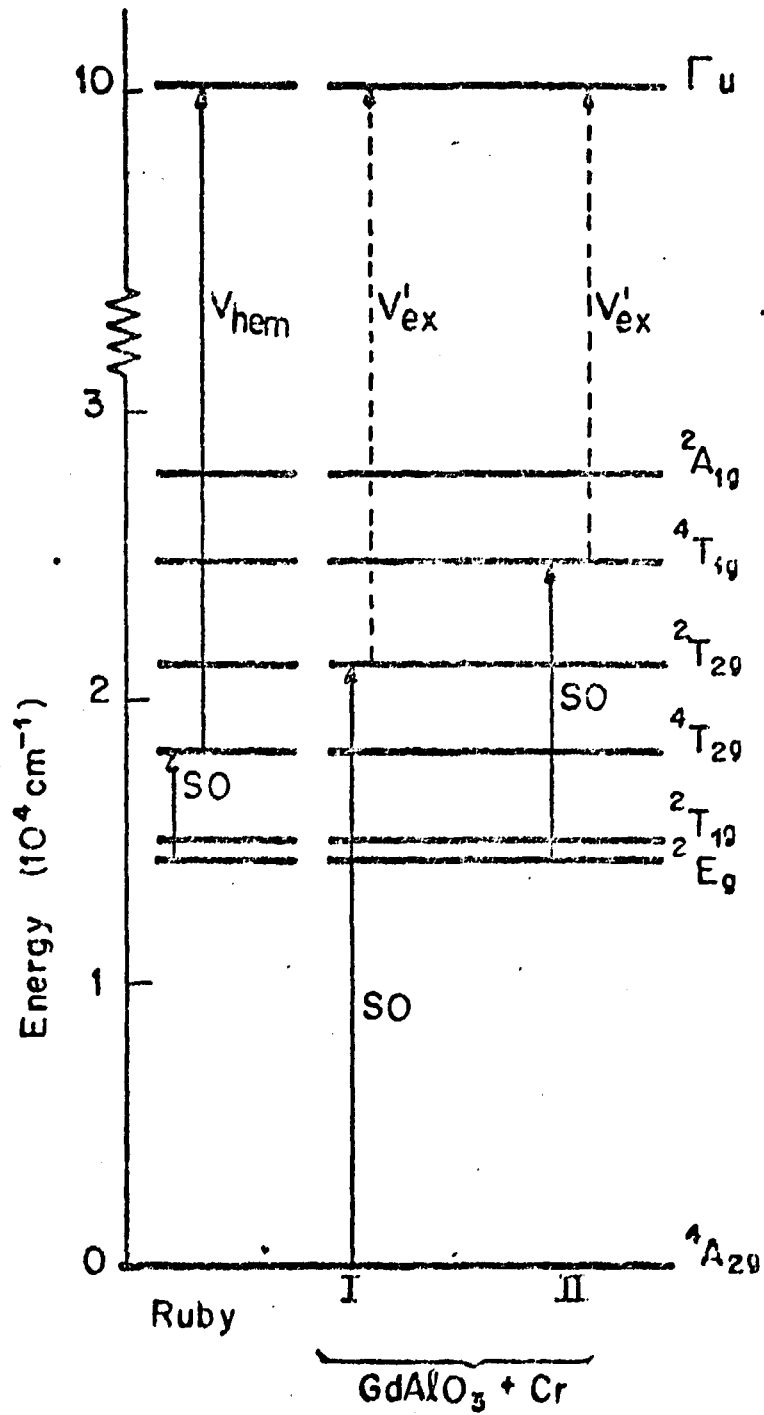


Fig. 1

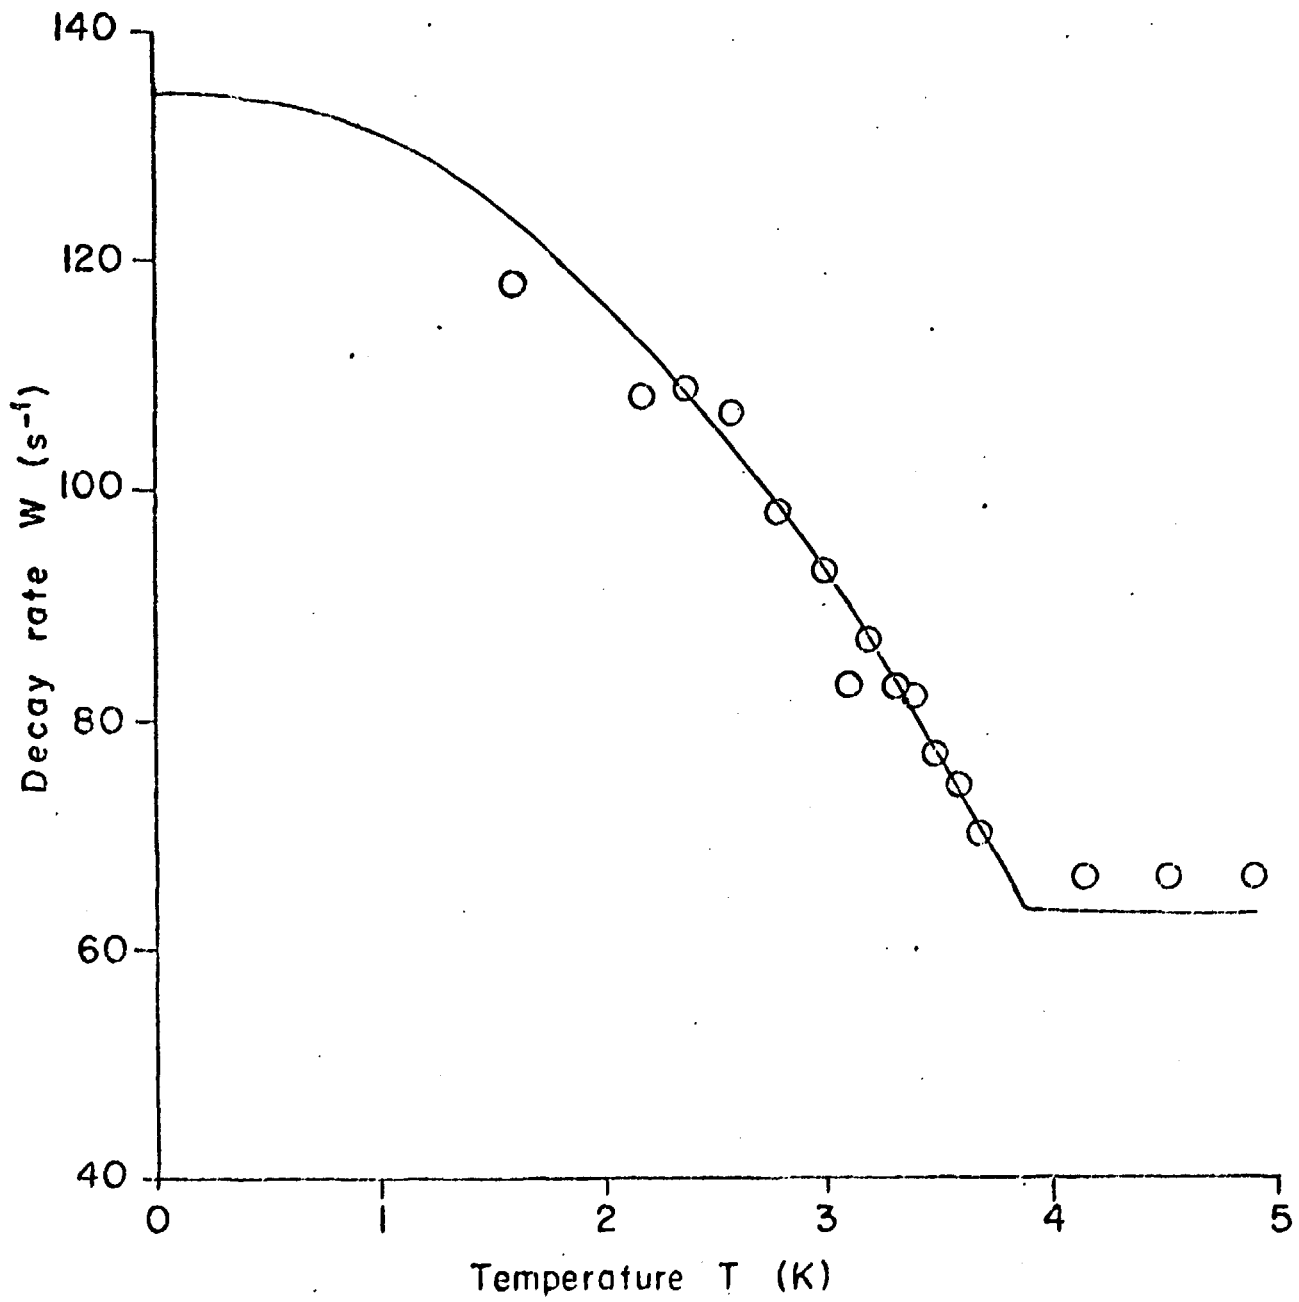


Fig. 2

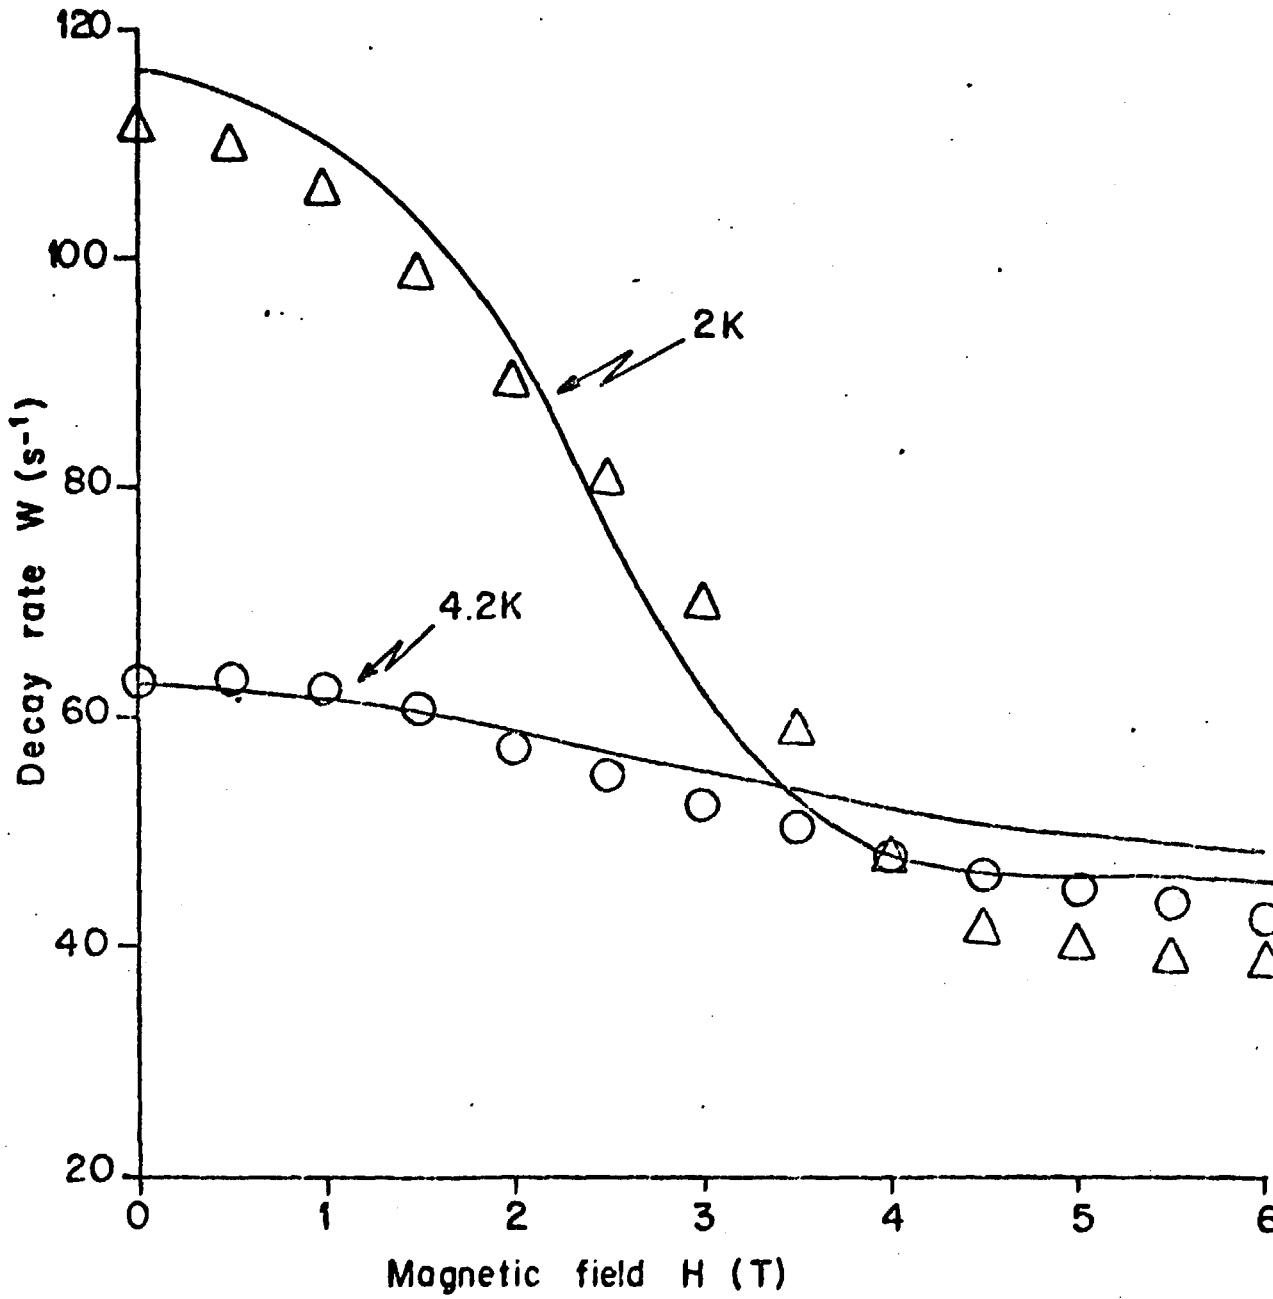


Fig. 3

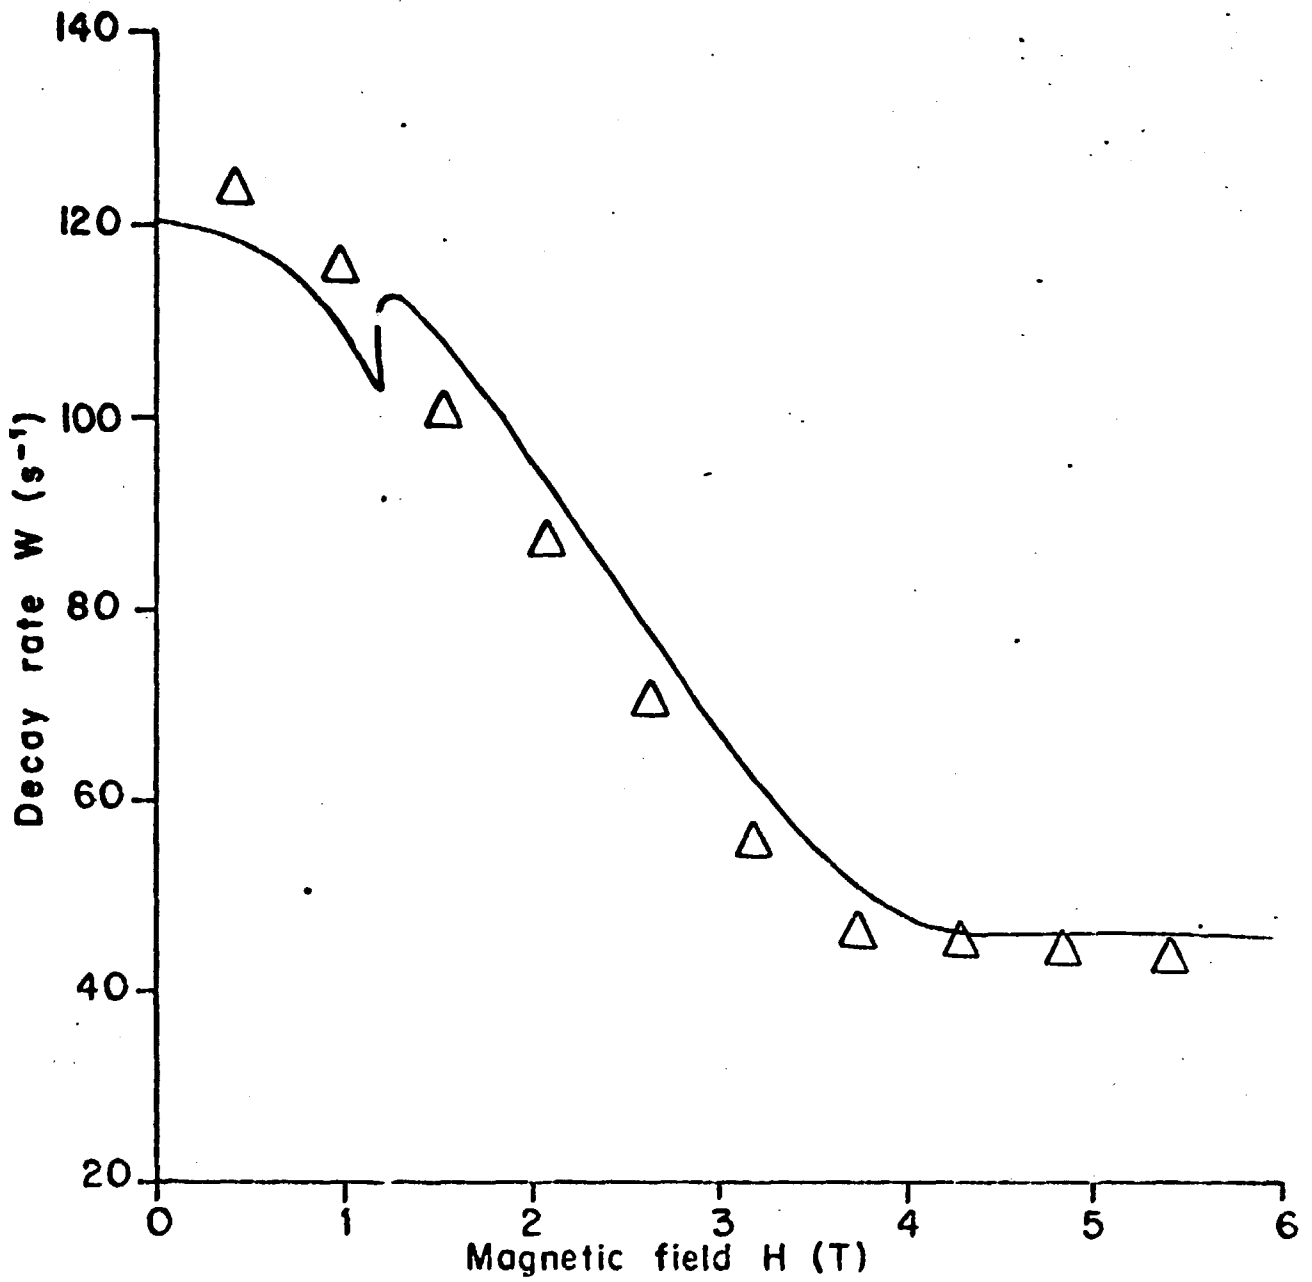


Fig. 4



## REFERENCES

- 1) R. C. Ohlman, R. Mazelski and J. Murphy, Technical Summary Report, ARPA Order No. 305, Code 4730, 1967, available from National Technical Information Service, Department of Commerce, 5285 Port Royal Road, Springfield, VA 22161, USA.
- 2) K. W. Blazey and G. Burns, Proc. Phys. Soc. London 91, 640 (1967).
- 3) K. W. Blazey and H. Rohrer, Phys. Rev. 173, 574 (1968).
- 4) J. Murphy and R. C. Ohlman, *Optical Properties of Ions in Crystals*, ed. H. M. Crosswhite and H. W. Moos (Interscience, New York, 1969) p. 239.
- 5) K. W. Blazey, H. Rohrer and R. Webster, Phys. Rev. B 4, 2287 (1971).
- 6) J. S. Helman, J. Phys. Chem. Solids 32, 251 (1971).
- 7) J. S. Helman, R. A. Carvalho, H. Panepucci, M. C. Terrile, M. A. Aegerter and E. Soarez, Solid State Commun. 31, 1015 (1979).
- 8) M. A. Aegerter, H. C. Basso and H. J. Scheel, Proc. Int. Conf. on Lasers '80, Dec 15-19 (1980).
- 9) J. S. Helman and W. Baltensperger, Phys. Rev. B 25, 6647 (1982).
- 10) J. Mustre de Leon, J. S. Helman and G. Cisneros, Solid State Commun. 46, 841 (1983).
- 11) M. Matsuoka, M. A. Aegerter, H. Panepucci, M. C. Terrile, J. S. Helman and H. J. Scheel, Phys. Rev. Letters 50, 204 (1983).
- 12) J. S. Helman, Phys. Rev. 39, 3389 (1989).
- 13) M. del Castillo-Mussot, D. Guenzburger and J. S. Helman, to be published in J. Magn. Mag. Mat. 1990.
- 14) H. J. Scheel and E. O. Schulz-Dubois, J. Cryst. Growth 8, 304 (1971).

- 15) H. J. Scheel, *J. Cryst. Growth* 13/14, 560 (1972).
- 16) G. F. Imbusch, in *Luminescence Spectroscopy*, ed. by M. D. Lumb, Academic Press, New York, 1978, p. 27.
- 17) S. Sugano and Y. Tanabe, *J. Phys. Soc. Japan* 13, 880 (1958).