

Relationship between Carbon Microstructure, Adsorption Energy and Hydrogen Adsorption Capacity at Different Temperatures

Jacek Jagiello and Matthias Thommes

Quantachrome Instruments, 1900 Corporate Drive, Boynton Beach, Florida 33426, USA

Various microporous materials such as activated carbons, nanotubes, synthetic microporous carbons as well as metal organic framework materials are being considered for hydrogen storage applications by means of physical adsorption. To develop materials of practical significance for hydrogen storage it is important to understand the relationships between pore sizes, adsorption energies and adsorption capacities. The pore size distribution (PSD) characterization is traditionally obtained from the analysis of nitrogen adsorption isotherms measured at 77 K. However, a portion of the pores accessible to H₂ may not be accessible to N₂ at this temperature. Therefore, it was recently proposed to use the DFT analysis of H₂ adsorption isotherms to characterize pore structure of materials considered for hydrogen storage applications [1]. In present work, adsorption isotherms of H₂ and N₂ at cryogenic temperatures are used for the characterization of carbon materials. Adsorption measurements were performed with Autosorb 1 MP [Quantachrome Instruments, Boynton Beach, Florida, USA].

As an example, Fig 1 compares PSDs calculated for the activated carbon sample (F400, Calgon Carbon) using combined H₂ and N₂ data, and using N₂ isotherm only. The nitrogen derived PSD does not include certain amount of micropores which are accessible to H₂ but not to N₂ molecules. Obviously, the difference in the calculated PSDs by the two methods will depend on the actual content of small micropores in a given sample.

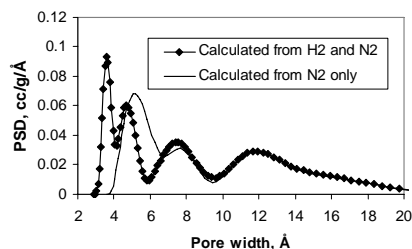


Fig. 1. PSDs calculated for F400 (Calgon Carbon) sample.

Carbon adsorption properties can also be characterized by the isosteric heat of adsorption, Q_{st} , related to the adsorption energy and dependent on the carbon pore/surface structure. Fig 2 shows Q_{st} data calculated using the Clausius-Clapeyron equation from H₂ isotherms measured at 77 K and 87 K for the carbon molecular sieve CMS 5A (Takeda), oxidized single wall nanotubes (SWNT) [2], and graphitized carbon black (Supelco). The Q_{st} values decrease with increasing pore sizes. The highest Q_{st} is observed for the CMS sample

having micropores sizes of about 5 Å. The SWNT sample shows a lower Q_{st} due to its relatively wide PSD [2], and the nonporous carbon black is characterized by the lowest Q_{st} values.

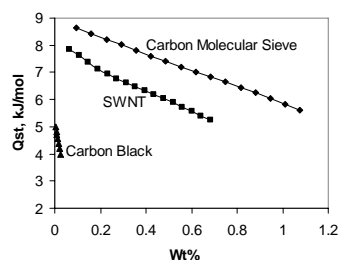


Fig. 2. Isosteric heats of H₂ adsorption for carbon molecular sieve 5A, single wall nanotubes, and graphitized carbon black.

The Q_{st} values calculated from H₂ adsorption isotherms measured at cryogenic temperatures below 1 atmosphere can be used to predict/estimate H₂ adsorption at ambient temperatures under high pressures. Fig 3 shows the H₂ adsorption isotherm on the SWNT sample calculated for 298 K from the low-pressure and low temperature (77, 87 K) data using the Clausius-Clapeyron equation and assuming the temperature independence of the Q_{st} values. A good agreement with high-pressure experimental data [3] is observed.

Predictions using DFT model will also be discussed during presentation.

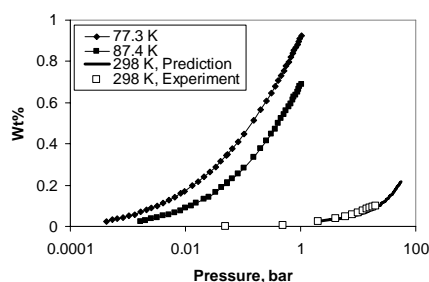


Fig. 3. Hydrogen adsorption on SWNT at 298 K (continuous line) calculated from measurements at 77 and 87 K. High pressure experimental data (open squares) ref. [3].

- [1] J. Jagiello, M. Thommes, *Carbon* **42**, 1227, 2004.
- [2] A. Ansón, J. Jagiello, J. B. Parra, M.L. Sanjuan, A. M. Benito, W. K. Maser, M. T. Martínez, *J. Phys. Chem. B*, **108**, 15820, 2004.
- [3] A. Ansón, M. Banham, J. Jagiello, M. A. Callejas, A. M. Benito, W. K. Maser, M. A. Zuttel, P. Sudan, M. T. Martínez, *Nanotechnology*, **15**, 1503, 2004.