
FATIGUE TESTING ON SAMPLES FROM ZIRCALOY-4 TUBES TYPE SEU-43

Valentin OLARU, Viorel IONESCU, Alexandru NITU, Dragos IONESCU, Florea VOICU

**Institute for Nuclear Research, Pitesti, Romania
valentin.olaru@nuclear.ro*

ABSTRACT

The paper presents the testing of samples worked from Zircaloy-4 tubes (“as-received” metallurgical state), utilized in the composition of the CANDU SEU-43 fuel bundle. These tests are intended to simulate their behaviour in a power cycling process inside the reactor. The testing process is of low cycle fatigue type, done outside of the reactor, on “C-ring” samples, cut along the transversal direction. These samples are tested at 1%, 2% and 3% amplitude deformation, at room temperature. The calibration curves for both types of tube (small and big diameter) are determined by using the finite element analyses with the ANSYS computer code.

The cycling test results are in the form of a fatigue life curve ($N-\epsilon$) for zircaloy-4 used in the SEU-43 fuel bundle. The curve is determined by the experimental dependency between the number of cycles to fracture and the deformation amplitude. The low cycle fatigue mechanical tests done at room temperature together with electronic microscopy analyses have reflected the characteristic behaviour of the zircaloy-4 metal in the given environment conditions.

Key words: low cycle fatigue, SEU-43, room temperature, ANSYS computer code

Introduction

Presently, the CANDU type reactors use a fuel bundle made up of 37 rods filled with natural uranium pellets. The functionality of the current fuel at extended burn degrees doesn't offer the desired performance. Because of this fact, a new fuel bundle concept, named SEU-43, was proposed. This new concept uses low enriched uranium, obtained from the reprocessing of burnt fuel in LWR type reactors. The SEU-43 fuel bundle represents an evolution of the standard CANDU fuel bundle with 37 elements.

Based on a technology developed at ICN Pitesti and on material specifications and fabrication tolerance imposed through the SEU-43 fuel bundle project, attempts were made to formulate a series of demands which will constitute the base for a quality control plan focused on ICN's own experimental research.

In this paper, a mechanical testing of Zircaloy-4 is presented. This material is used in the forging of two different diameter (small and big) tubes used to encapsulate the SEU-43 fuel.

The fatigue tests done outside the reactor for non-irradiated Zircaloy-4 tubes were thought up and realised at ICN. These fatigue tests will help in estimating the durability curves and other parameters that influence fatigue behaviour.

The testing process is of low cycle fatigue type, done outside the reactor, on “C-ring” samples, cut along the transversal direction. These samples are tested at 1%, 2% and 3% amplitude deformation, at room temperature.

The testing equipment for “C-ring” samples was built at ICN and is capable of performing fatigue tests, being able to control displacement in the horizontal plane with the help of the proper transducer. For every sample deformation (1%, 2%, 3%), there is a corresponding displacement of the piston, measured by the transducer in millimetres.

The durability curve represents the fatigue behaviour of the cladding material. In this case it is obtained for room temperature. In the current paper, having in mind the absence of high temperature resistant strain gages, the deformation calibration of “C-ring” samples, was done using finite element analysis in the ANSYS computer code [5].

Using the experimental data resulted from the tests, the durability curves are graphically traced for each type of sample (big and small diameter) and for metallurgical and microstructural state mentioned in the testing matrix.

Experimental set-up

The fatigue testing equipment (Fig.1.) was designed and built in 2002 at ICN [7] and is used to test multiple types of samples.



Fig.1. *The equipment used for simulated power cycling fatigue*

The sample holders (Fig.2.) are two “yoke”-like pieces, one of which is fixed to the support beam of the testing chamber, the other being coupled with a crank gear system, necessary for cyclic movement.



Fig.2. Sample holders

The command and data acquisition operations are handled by the Split Monitor Software. This application is developed and adapted for the Windows XP Operating System.

Sampling Process

The ring shaped samples (Fig.3.) were cut from Zircaloy-4 tubes.

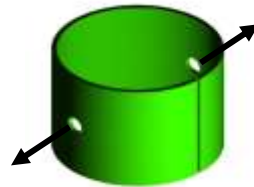


Fig.3. C-ring sample

Establishing the Calibration Curves

The calibration curves are dependent on the metallurgical state, as well as on the mechanical and microstructural characteristics of the material. These curves represent the dependency between the central deformation of the sample and the displacement of the piston, variables which can be measured with a strain gage and a displacement transducer. Every deformation (1%, 2% and 3%) is equivalent to a certain displacement of the piston which is measured by the transducer in millimetres.

Having in mind that the measuring of the deformation poses the most difficulties because of the small dimensions of the sample, the elaborate techniques utilized for attaching the strain gages and the lack of high temperature resistant strain gages, an alternative was chosen to obtain the calibration curves: the finite element analyses in the ANSYS computer code [5].

Using this method, the calibration curves for the 1% ÷ 3% deformation domain were traced for “C-ring” samples, at room temperature. For this, a transversal cross-section of the specimen was modelled (Fig.4.).



Fig.4. Modelling of “C-ring” samples using ANSYS

The code utilizes the material parameters (flow resistance, break and elastic deformation resistance)

determined with the following formulas: $\epsilon_{real} = \ln(1 + \epsilon_{exp})$

$\sigma_{real} = \sigma_{exp} \cdot (1 + \epsilon_{exp})$ -Where: ϵ_{real} is the calculated deformation
 σ_{real} is the calculated flow resistance

For determining mechanical properties, “ring tensile test” samples (Fig.5.) were used.



Fig.5. „Ring tensile test” samples

The experimental values were determined from the curves (Fig.6.) obtained from tensile tests at room temperature.

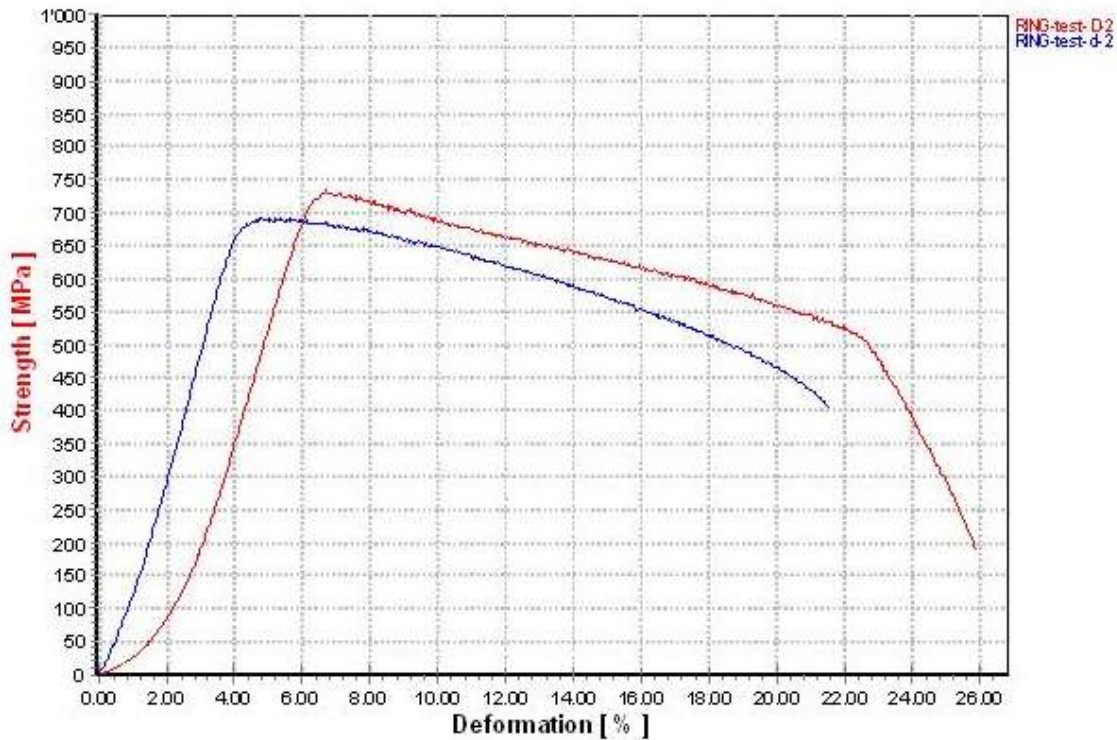


Fig.6. The experimental tensile curves for SEU-43 samples, big diameter (D) and small diameter (d), on the same graph

The mechanical parameters resulted from the calculated “real” curves are used for the ANSYS modelling. After the simulation, the results were compared with the results of calibrations done using strain gages and were found to be similar.

The Fatigue Tests

The fatigue tests which simulate power cycling conditions inside the reactor were executed in conformity with references [2], [3] and [6], and were done on the fatigue testing installation described in reference [7]. A series of five samples per deformation (1%, 2%, 3%), per diameter (small and big) were tested.

Results

The calibration curve is the graphical representation of the dependency between the central deformation of the sample and the displacement of the piston. The calibration curves obtained using the ANSYS code are represented in figure Fig.7. (SEU tip I – big diameter) and figure Fig.8. (SEU tip II – small diameter). The different curves are for calculations done in the central node and for mediation of multiple nodes starting from the central one. This mediation represents the length of the contact surface of the strain gage with the sample.

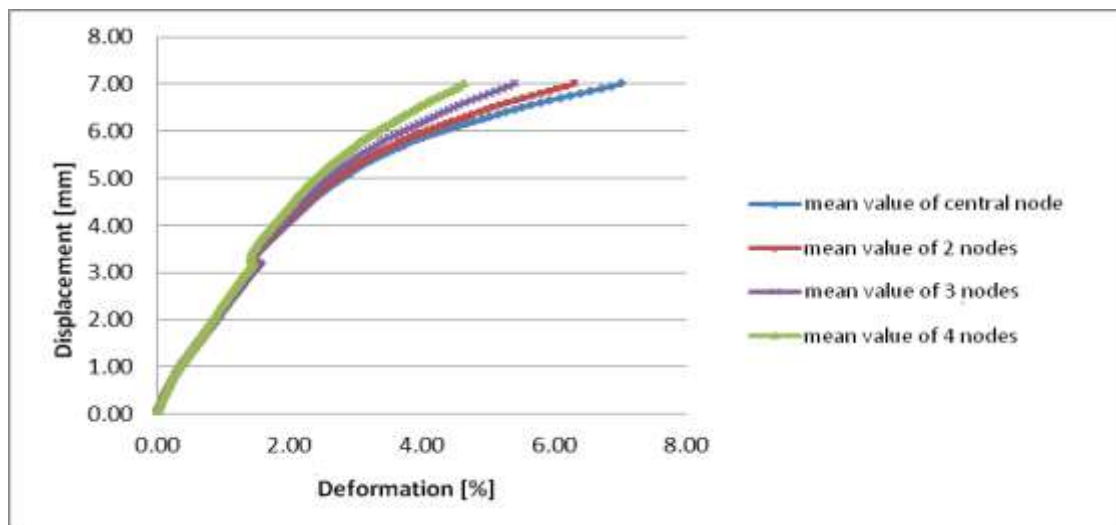


Fig.7. Deformation – piston displacement dependency at room temperature, when the fixing holes are drilled on the diameter axis of the big diameter (D) SEU-43 sample.

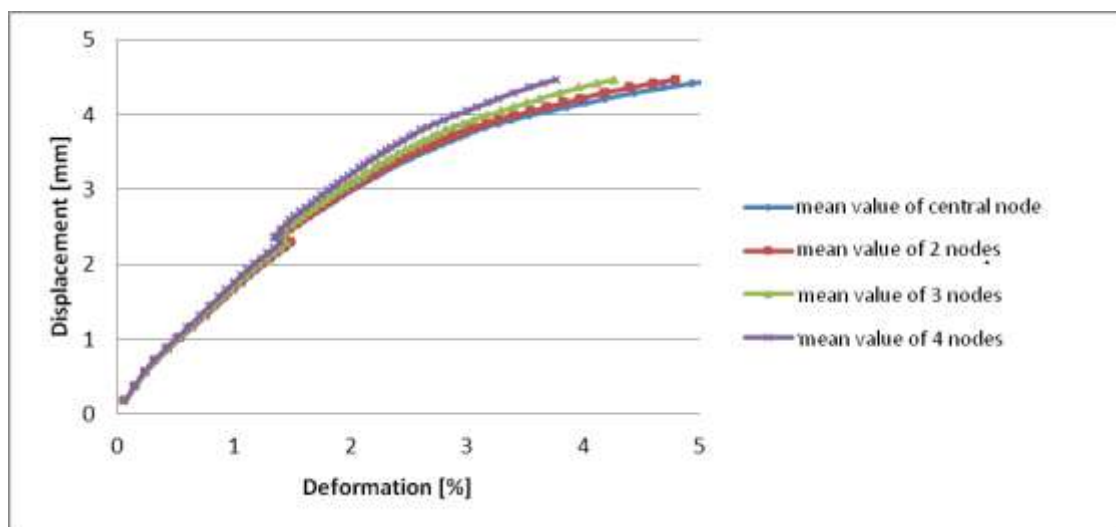


Fig.8. Deformation – piston displacement dependency at room temperature, when the fixing holes are drilled on the diameter axis of the small diameter (d) SEU-43 sample.

It was established for both diameters that the best representation of the dependency between the deformation (1%, 2%, 3%) and the piston displacement is correlated by the curve for the central node, corresponding to the smallest possible area of contact with a strain gage.

Determinating the Durability Curve

In Fig.9 and Fig.10 the experimental data are presented. Because of the very high number of cycles to fissure (>200k) at 1% deformation, in comparison with 2% and 3% deformation, a power function curve was fitted just for the 2% and 3% data. A comparison was made with previous papers ([6] and 8)).

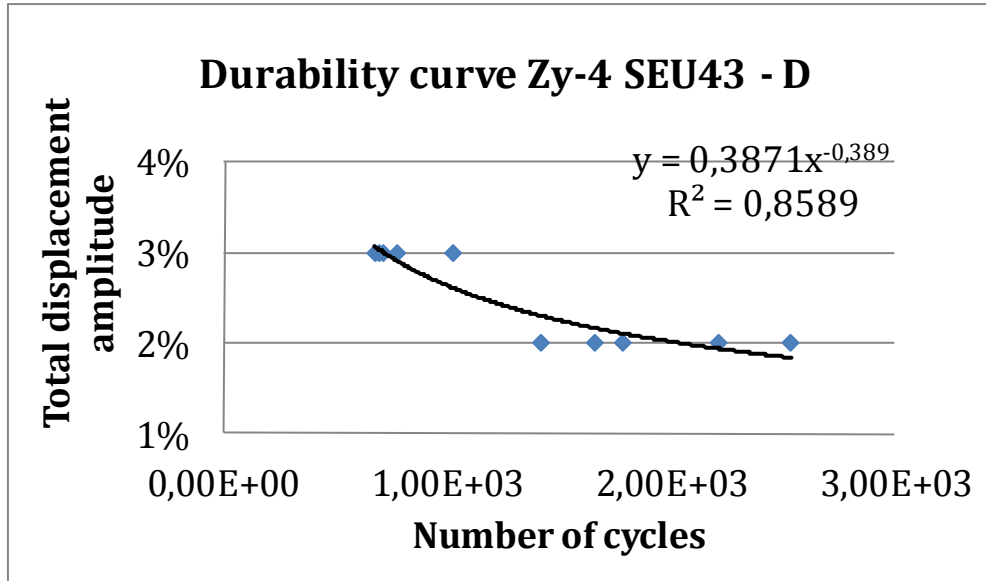


Fig.9. Durability Curve for Zircaloy-4, SEU-43, Big diameter(D) samples

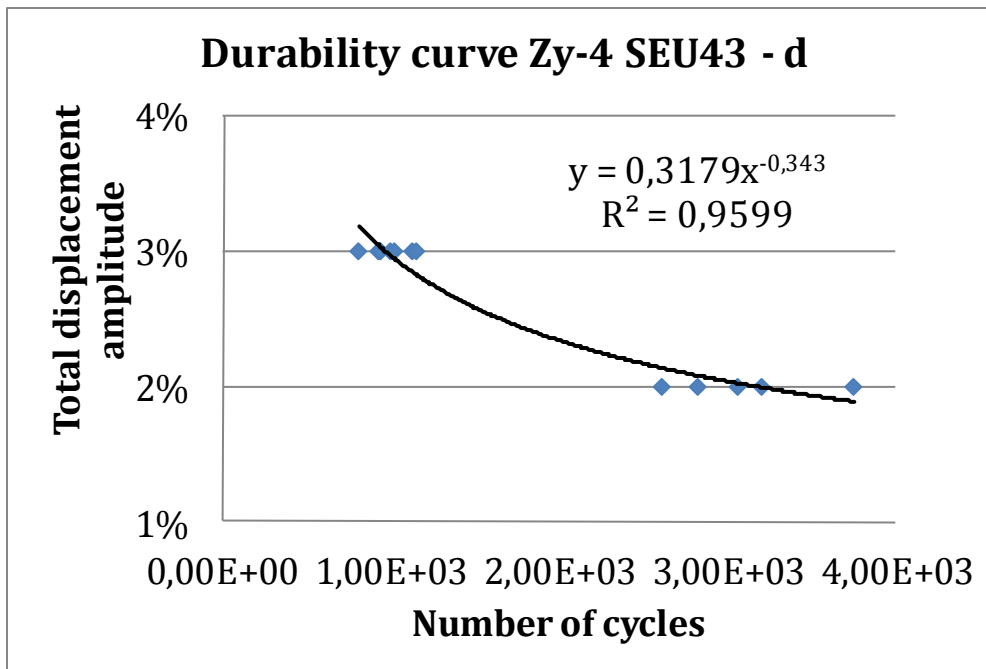


Fig.10. Durability Curve for Zircaloy-4, SEU-43, Small diameter(d) samples

Microstructural analysis of break surface

A SEM analysis was done on the room temperature fatigue test samples. In Fig.11 it is shown the different aspects of the break surface. The SEM analysis revealed the ductile-brittle break mode, done in phases along the fatigue striations, phenomenon present in all Zircaloy-4 fatigue tests.

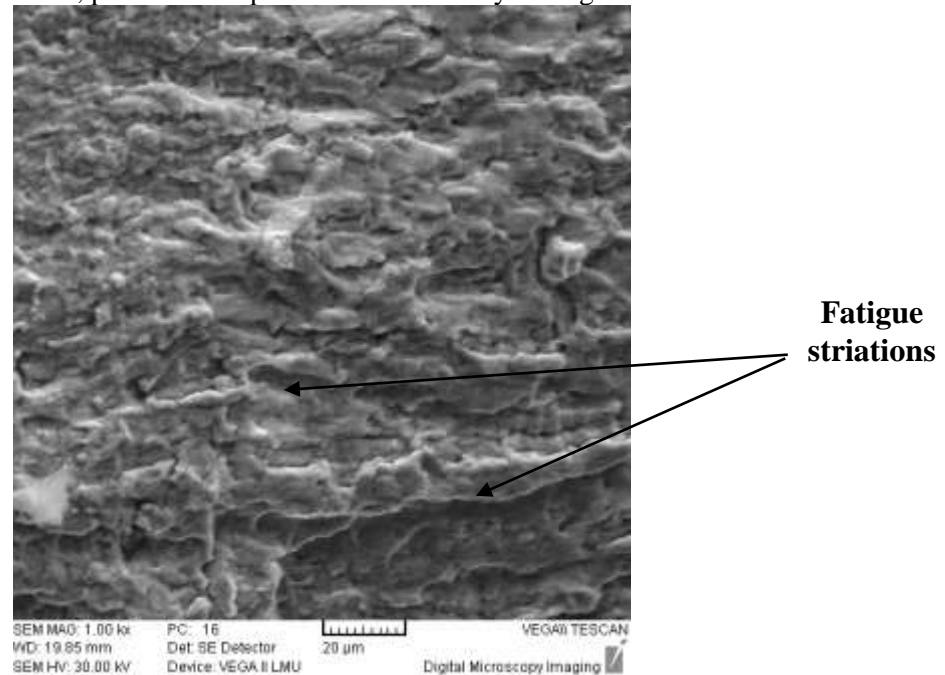


Fig.11. Zircaloy-4 break surface of fatigue sample at room temperature (x1000)

Conclusions

The fatigue tests described in this paper simulate power cycling conditions inside the reactor. The “C-ring” samples worked from Zircaloy-4 tubes (as received state) were tested using an installation designed and built at ICN. The tests were done at room temperature for 1%, 2% and 3% amplitude deformation in accordance with ref. [5].

For determining the calibration curves, the finite element analyses in the ANSYS computer code was used. The prediction capacity of the ANSYS simulation was verified in a previous project, comparing the results of the calibration with the results from using strain gages, and were found to be acceptably close.

The results include the durability curve describing the behaviour of “C-ring” samples worked from Zircaloy-4 tubes (as received state) subjected to low cycle fatigue tests done at 1%, 2% and 3% deformation amplitude.

The SEM analysis revealed the ductile- brittle break mode of the cycling fatigue tested samples.

References

- [1]. M. Roth, V. Pitigoi, M Mihalache, “Simularea comportarii tecii elementului combustibil CANDU in conditii de ciclaj de putere prin teste in afara reactorului. Raport final”, R.I. 8094/2008
- [2]. M. Roth, V. Pitigoi, Fl. Savu, “Punerea in functiune a instalatiei pentru simularea comportarii in conditii de ciclaj de putere a tecilor de zircaloy”, R.I. 6443/2002.

-
- [3]. V. Pitigoi, M. Roth, V. Radu, “Comportarea tecilor de Zircaloy-4 in regim de ciclaaj de putere”, R.I. 6714/2003.
- [4]. Specificatie de testare, “Teste de ciclaaj in afara reactorului, care stimuleaza variatiile de putere ale combustibilului CANDU”, INR-372000-400-002, Rev.0
- [5]. ANSYS 7.1 Documentation
- [6]. M. Roth, V. Pitigoi, “Testarea tuburilor de Zircaloy-4 (Furnitura AECL) in regim de ciclaaj de putere”, R.I. 6929/2004.
- [7]. F. Savu, “Instalatie pentru simularea comportarii in conditii de ciclaaj de putere a tecilor de Zircaloy-4”, SCN – R.I. 6357/2002.
- [8]. V. Pitigoi, M. Roth, Al. Nitu, F. Voicu, “teste de ciclaaj pe probe prelevate din tuburi de zircaloy-4”, R.I. 8853/2010